

AD-A154 887

SYNTHESIS OF ENERGETIC MATERIALS(U) NAVAL SURFACE  
WEAPONS CENTER WHITE OAK LAB SILVER SPRING MD  
H G ADOLPH ET AL. 31 MAR 85

**1/1.**

UNCLASSIFIED


F/G 7/3

NL

END

FILMED

D-11C

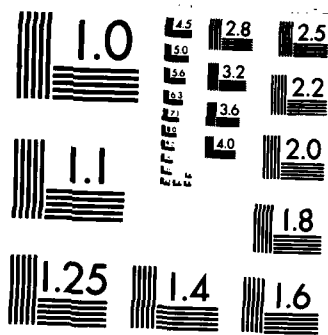

MICROCOPY RESOLUTION TEST CHART  
NATIONAL BUREAU OF STANDARDS-1963-A

AD-A154 887

SYNTHESIS OF ENERGETIC MATERIALS  
ANNUAL PROGRESS REPORT FOR THE  
OFFICE OF NAVAL RESEARCH

WORK REQUESTS N0001484WR24121 AND  
N001485WR24088  
PROJECT RR024-02-01/02-0D

By H. G. Adolph  
M. Chaykovsky  
J. M. Goldwasser  
W. M. Koppes  
T. C. Adams, Jr.

March 1985


Research and Technology Department

NAVAL SURFACE WEAPONS CENTER  
Dahlgren, VA 22448 - Silver Spring, MD 20903-5000

Reproduction in whole or in part is permitted  
for any purpose of the United States Government.

Approved for public release; distribution unlimited.

DTIC FILE COPY

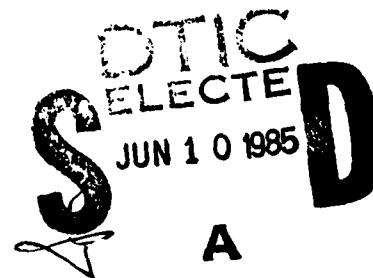

Enclosure (1)

85 5 14 008

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER	2. GOVT ACCESSION NO. AD-A154887	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle)  Synthesis of Energetic Materials		5. TYPE OF REPORT & PERIOD COVERED Annual Progress Report 1984
		6. PERFORMING ORG. REPORT NUMBER
7. AUTHOR(s) H. G. Adolph, M. Chaykovsky, J. M. Goldwasser, W. K. Koppes, and T. C. Adams, Jr.		8. CONTRACT OR GRANT NUMBER(s) Work Request N0001484WR24121 N0001485WR24088
9. PERFORMING ORGANIZATION NAME AND ADDRESS Naval Surface Weapons Center (Code R11) White Oak, Silver Spring, Maryland 20903-5000		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS  61153N;RR024-02
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research Code 432 Arlington, Virginia 22217		12. REPORT DATE 31 March 1985
		13. NUMBER OF PAGES
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		15. SECURITY CLASS. (of this report)  UNCLASSIFIED
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report)  Approved for public release; distribution unlimited.		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		
18. SUPPLEMENTARY NOTES  Reproduction in whole or in part is permitted for any purpose of the United States Government.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number)  Nitrodiols; Polyformals; Nitropolymers; Nitramines; Diazocines; Azabicyclononanes; Azaadamantanes.		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The synthesis of polyformals from several nitro- and fluorodiols was in- vestigated. Linear, difunctional polyformals were obtained from 3,3,5,7,7- pentanitro-5-azanonanediol, 3,5,5,7-tetranitro-3,7-diazanonanediol, 2,2,3,3, 4,4-hexa fluoropentanediol, and 2,2,3,3,4,4,5,5-octafluorohexanediol. Procedures are given to prepare stable gumstocks from the first 3 of these, using FEFO as plasticizer. The fourth polymer was only partially miscible with FEFO.		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE  
S/N 0102-014-6601

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

20. Abstract

Efforts toward the synthesis of polyazabicyclooctanes and polyazaobicyclo-  
nonanes were continued. An acyclic model compound for the latter system was  
synthesized and found to be marginally stable. Various approaches to the  
synthesis of azacyclooctadienes as precursors to bicyclononanes were investigat-  
ed. A study of the chemistry of the 2,6-diazabicyclooctane ring system was  
initiated. Condensation reactions of 2,3-disubstituted and 2,3,5,6-tetrasub-  
stituted 1,4-dinitropiperazines with methylene diamine derivatives were  
investigated in efforts to prepare linear polycyclic nitramines. During  
this work, the first example of a 1,2-dinitraminoolefin was prepared. A  
new oxidizer of exceptionally high oxygen content, 2,3,5,6-tetranitrato-  
1,4-dinitropiperazine, was prepared but was found to decompose slowly at  
room temperature. Originator Supplied Keywords include)

At.



SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

## CONTENTS

	<u>Page</u>
Introduction.....	1
Energetic Polymer and Monomer Synthesis.....	1
Synthesis of Potentially Dense Nitramines.....	9
Experimental Section.....	27
References.....	36
Distribution.....	(1)

## ILLUSTRATIONS

<u>Figure</u>		<u>Page</u>
1	GP Chromatogram of a Polyformal of <u>1</u> from modified procedure .....	3
2	GP Chromatogram of Polyformal of <u>2</u> .....	4
3	GP Chromatogram of Polyformal of <u>3</u> .....	6
4	GP Chromatogram of Polyformal of $\text{HOCH}_2(\text{CF}_2)_3\text{CH}_2\text{OH}$ .....	8
5	GP Chromatogram of Polyformal of $\text{HOCH}_2(\text{CF}_2)_3\text{CH}_2\text{OH}$ ; Improved Procedure .....	10
6	GP Chromatogram of Polyformal of $\text{HOCH}_2(\text{CF}_2)_4\text{CH}_2\text{OH}$ .....	11

## SYNTHESIS OF ENERGETIC MATERIALS


### INTRODUCTION

The work described in this report was carried out during 1984 under the sponsorship of the Office of Naval Research, Code 432P (Dr. R. S. Miller). The effort consisted of two separate tasks which will be discussed in turn: (1) synthesis of energetic monomers and polymers, and (2) synthesis of polycyclic and adamantoid nitramines. Both tasks were continuations of previous work, and pre-1984 results are reported in ref. 1. The principal objectives of the work are the synthesis of energetic (nitro) polymers with improved energy and physical properties, specifically polyformals derived from nitro substituted diols, and the synthesis of nitramines with high crystal density and energy-density greater than HMX.

### ENERGETIC POLYMER AND MONOMER SYNTHESIS



In continuation of the previous work<sup>1</sup> under this task, the formation of hydroxy-terminated polyformals from selected nitro- and fluorodiols was investigated further.

It has been shown in the earlier work that 3,3,5,7,7-pentanitro-5-azanonediol (1) on reaction with  $\text{CH}_2\text{O}/\text{BF}_3$  etherate formed a mixture of linear and some cyclic polyformals, the former being hydroxy-terminated and thus cross-linkable with di/triisocyanates. These polymers were readily soluble in FEFO, and the FEFO solutions were readily cured with PAPI-135.

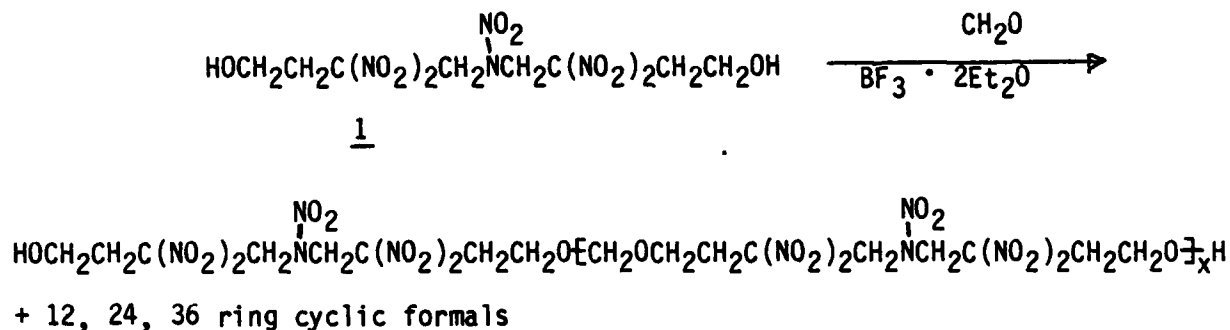


However, formation of bubbles thought to be due to residual formaldehyde was observed during the cure. During this year's effort a new sample of the polymer was prepared by the previous procedure,<sup>1</sup> except that a treatment of the crude polymer with hydrogen peroxide was added. FEFO solutions of this sample cured well without bubbling in several attempts, but produced a few bubbles in others. A larger quantity of the polymer was then prepared from 30g of the diol 1 by the modified procedure. The polymer yield was 25g ( $M_n \approx 2800$ ); based on the GPC (Fig. 1) and hydroxy group determinations, the cyclic formal content was estimated to be 8%. The curing of this polymer was studied in an effort to determine the cause of and alleviate the residual bubbling during cure. It was found that a good cure and void-free gumstocks could be obtained by the addition of <1% each of N-methyl-4-nitroaniline and N-phenyl-2-nitroaniline. These gumstocks had an excellent elongation and tear strength. About 20g of the polymer are available for further evaluation.

Some additional work was carried out on the synthesis of 1. The previously reported synthesis<sup>1</sup> of potassium 3,3-dinitropropanoate was repeated on a 50g scale, and the initially obtained yields were confirmed. The conversion to 3,3-dinitropropyl acetate was improved and now gives a 75% yield. The remainder of the synthesis of 1 remains unchanged. About 30g of 1 was prepared for conversion to the polyformal.

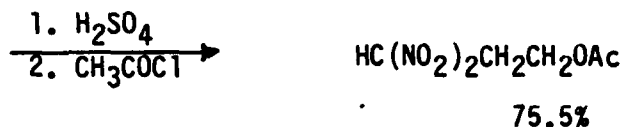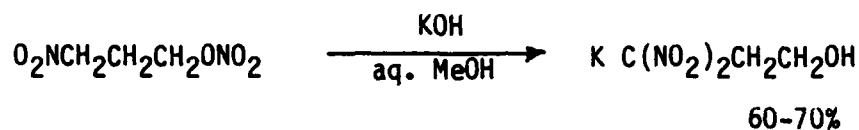

5g of pure diol 2 was prepared by the earlier<sup>1</sup> reported procedure, and the polymer formation with  $\text{CH}_2\text{O}/\text{BF}_3$  etherate in sulfolane was studied. Even under the best conditions found there was still about 30% cyclic formal in the

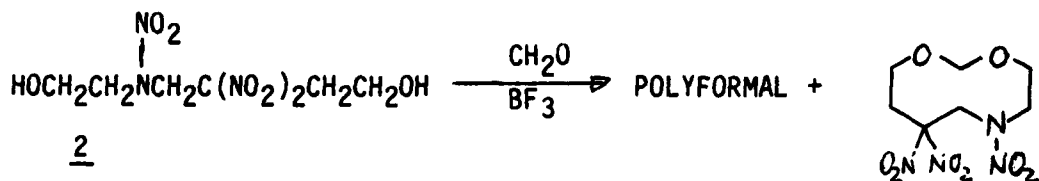

product mixture. The GPC of this material is shown in Fig. 2. Unless more favorable conditions can be found, 2 is therefore of questionable utility as a monomer in the polyformal reaction. No further work is planned at present.



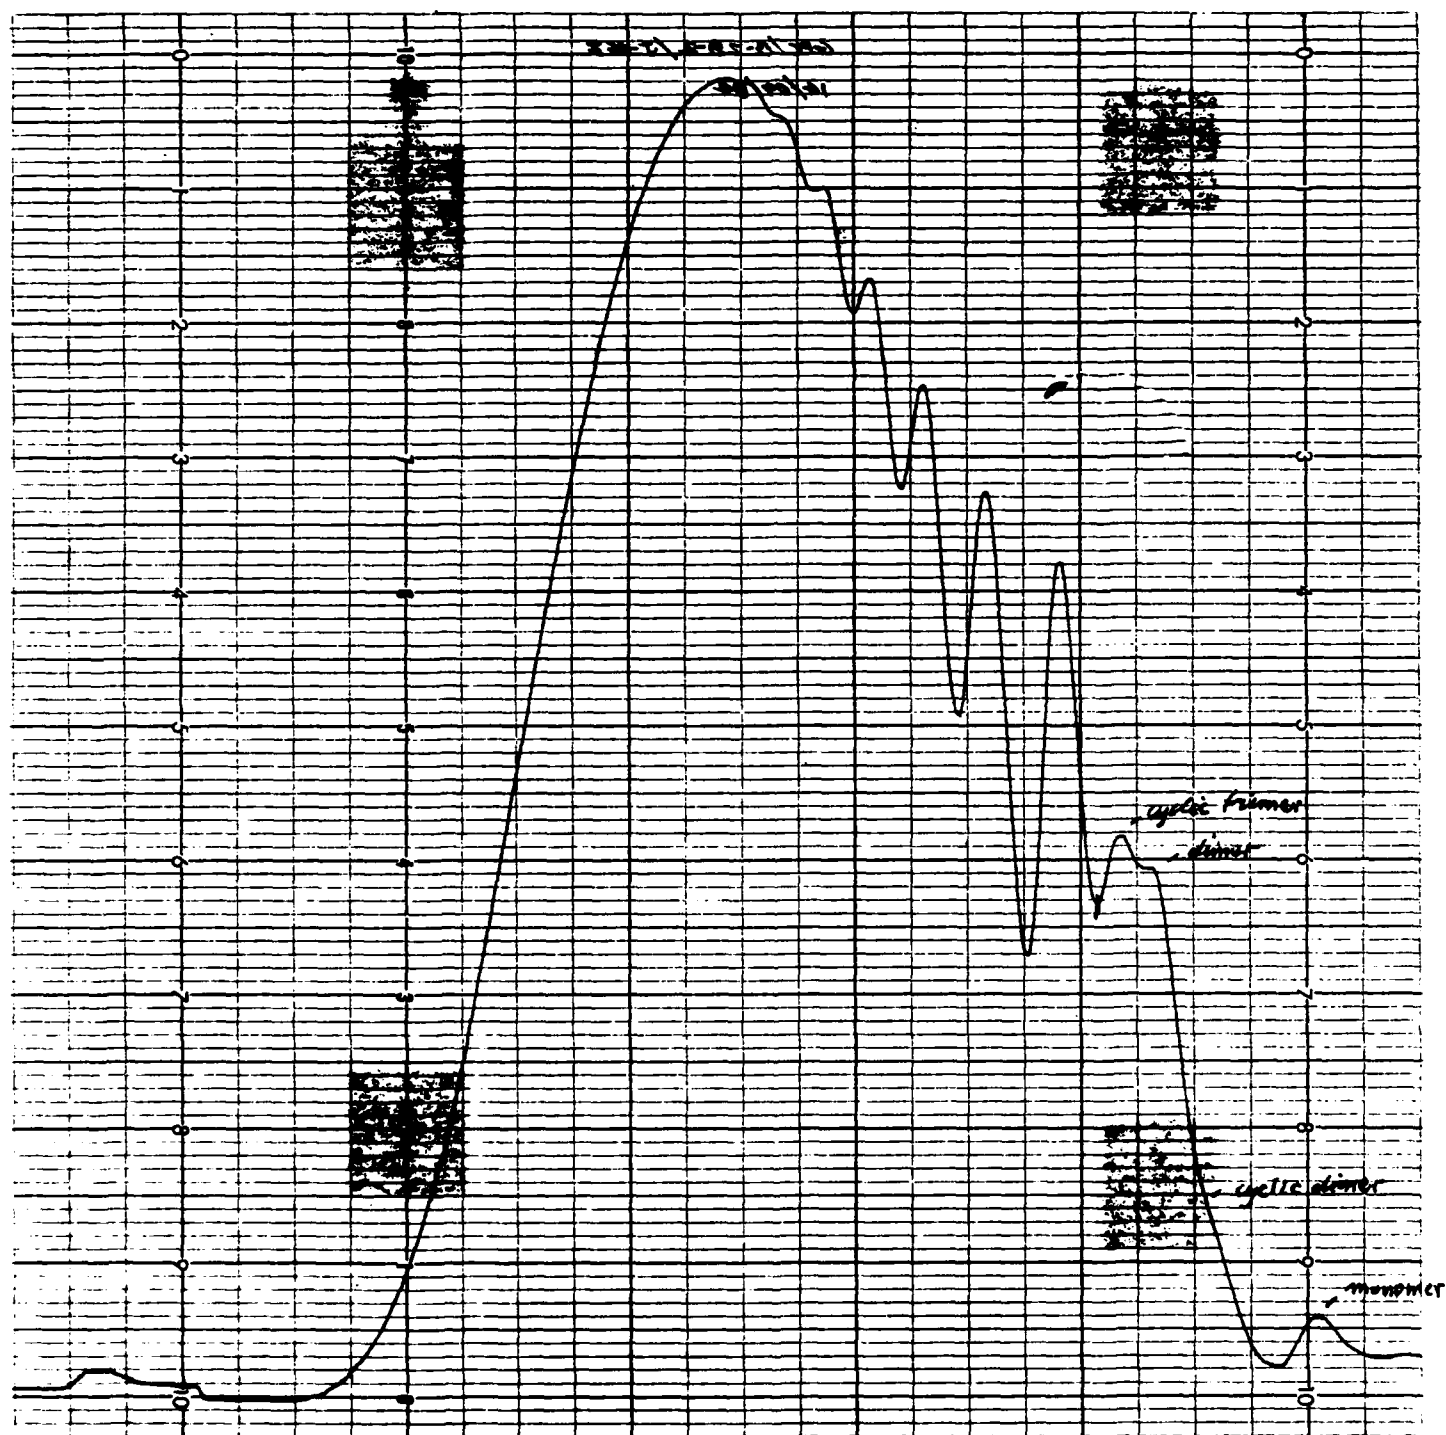


FIGURE 1. GPC OF POLYFORMAL OF 1 FROM MODIFIED PROCEDURE





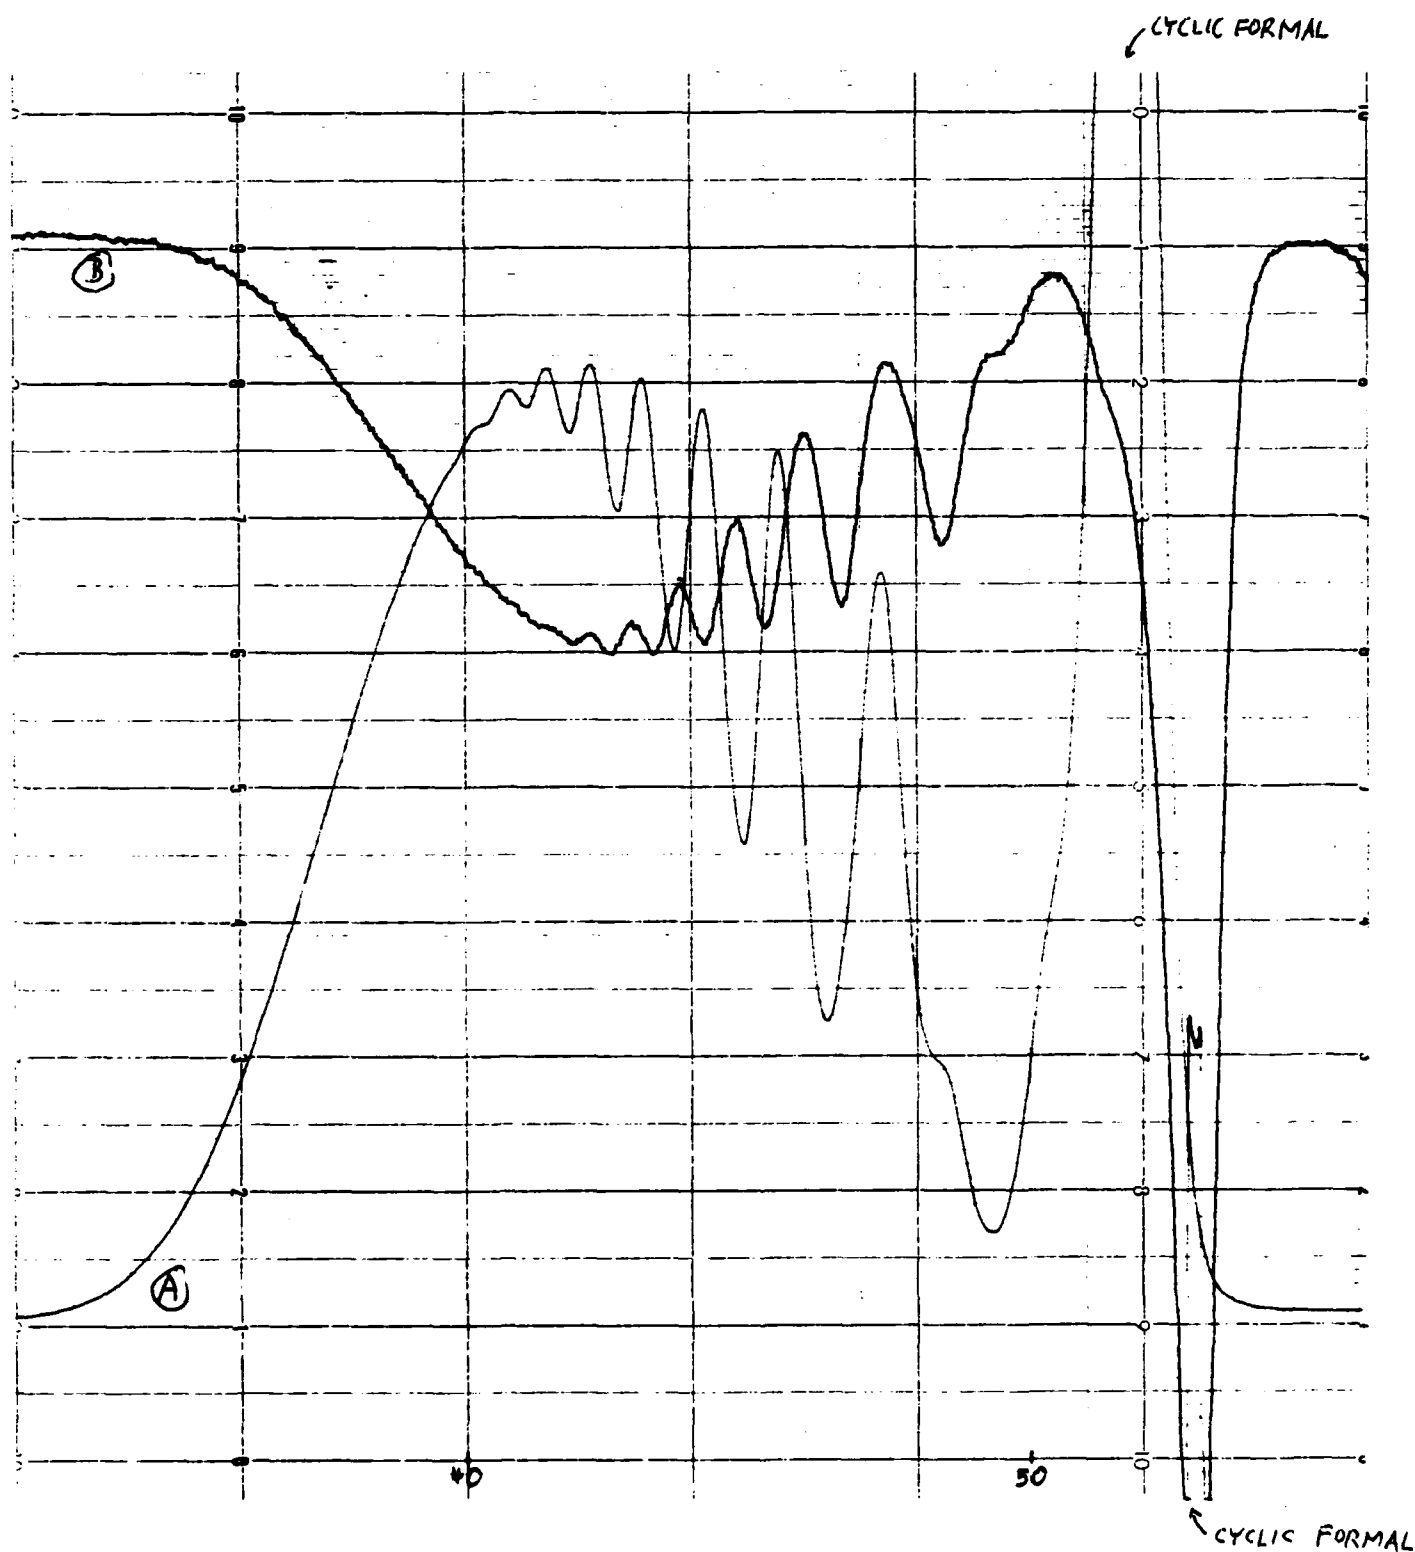




FIGURE 2. GPC OF POLYFORMAL OF 2; A: UV DETECTOR; B: RI DETECTOR

Diol 3 was synthesized recently to study the effects resulting from the exchange of nitramine for gem-dinitro groups and vice versa on the course of the reaction with formaldehyde and on the properties of the resulting polymer. Depending on the density, this polymer could be comparable in energy to that from 1. The synthetic approach to 3 is shown below:

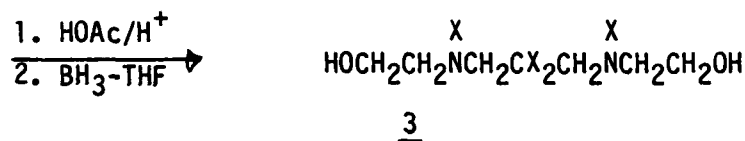

Ten grams of 3 was prepared by this method. The pure diol melted at 95-7°C, about 25° lower than 1. A polyformal ( $M_n \approx 3000$ ) was prepared from 3 in about 90% yield by reaction with trioxane in sulfolane with  $\text{BF}_3$  etherate as catalyst. The GPC (Fig. 3) and hydroxy group analysis indicated a cyclic formal content of only about 3%. Despite the lower melting point of 3, its polyformal was less soluble in FEFO than that from 1. However, a solution of 1 part of polyformal from 3 in 3 parts (w/w) of FEFO held at 60°C cured with PAPI-135/DBTDL to give a bubble-free gumstock which was stable to extended storage at room temperature (no phase separation). On the basis of these preliminary experiments it appears that the polyformal from 3 is more compatible with the gumstock components FEFO, PAPI-135, and DBTDL and is therefore more suitable as a binder component.

In previous work<sup>1)</sup> investigation of polyformal formation from fluorodiols 4 and 5 was initiated. Diol 4 was obtained commercially; the 3M Company<sup>2)</sup>



provided an experimental sample of diol 5. The polyformals of these diols were of interest because of anticipated miscibility with energetic plasticizers such as FEFO, which are not compatible with the more highly fluorinated commercial fluoropolymers such as 3 M's FC 2202 polyether and L 4093 functionalized Fluorel.


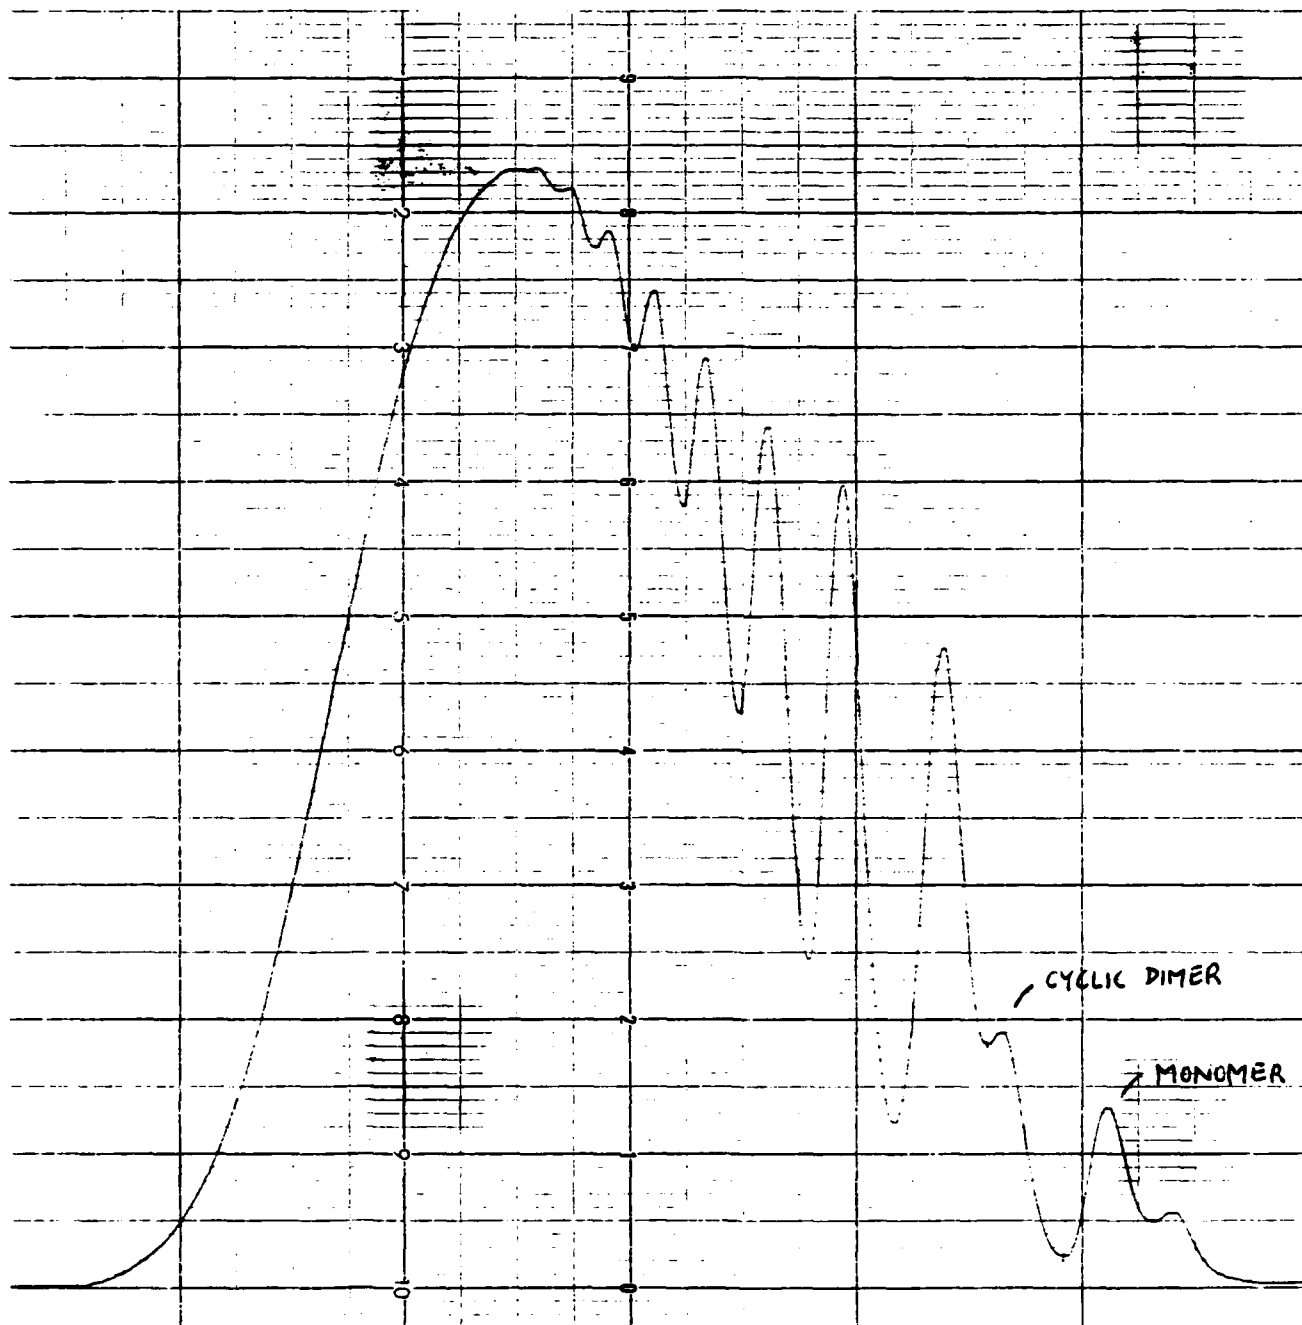


FIGURE 3. GPC OF POLYFORMAL OF 3

There are two reports in the literature of attempted preparations of polyformals of 4 and 5; in the case of 4, very low molecular weight polymers (m.w. 600-800) were obtained;<sup>3</sup> in the case of 5, the polymer was obtained from the cyclic formal, and the properties and m.w. were not determined.<sup>4</sup> In the work under this task, diol 4 was reacted with formaldehyde in approximately 85% sulfuric acid to give a mixture of polymer, unreacted monomer, and cyclic formals. The low molecular weight products were readily removed by heating

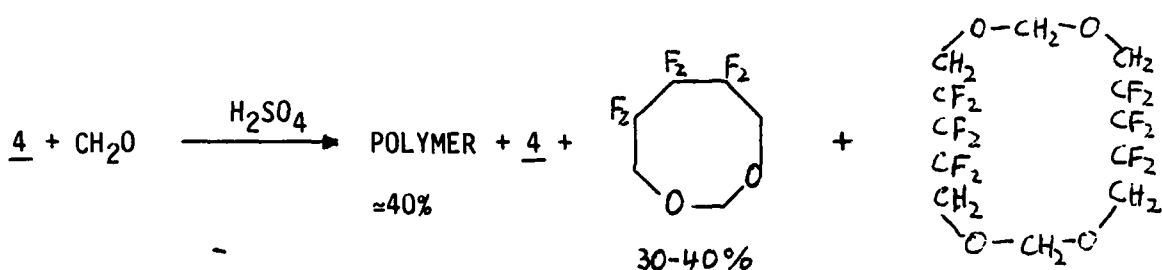


to 120°C in vacuo. The resulting polymers had molecular weights in the 3000-4000 range depending on the formaldehyde/monomer ratio. A larger scale run gave the material shown in Fig. 4 with the following characteristics:

OH equivalent weight: 2098 (includes about 5% of cyclic dimeric formal in the sample)

$\overline{M}_n$ : 4046  
Functionality  $\approx 2$

A gumstock prepared from a similar polymer of equivalent weight 1813 with FEFO as plasticizer (Pl:Po = 2:1) and PAPI-135/Dibutyltin dilaurate as curative was well cured after 2-3 days at 50°C and had a density of 1.59 g/cm<sup>3</sup>. The properties of this gumstock demonstrate excellent miscibility and compatibility of the polymer with FEFO.

An improved synthesis for hexafluoropentanediol polyformal was developed which gives improved yields and excellent molecular weight control over the range  $M = 2,000 - 20,000$ . The method consists of the conversion of the diol to hexafluorodioxocane with formaldehyde/triflic acid (>80% yield) followed by triflic acid catalyzed polymerization of an appropriate mixture of diol and dioxocane to produce the desired molecular weight. The polymer yield is 70-75%. Fluorodiol not converted to polymer can be recovered and recycled.

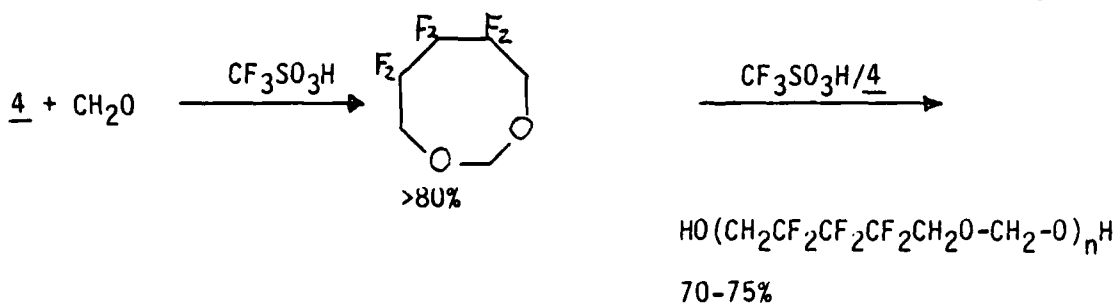



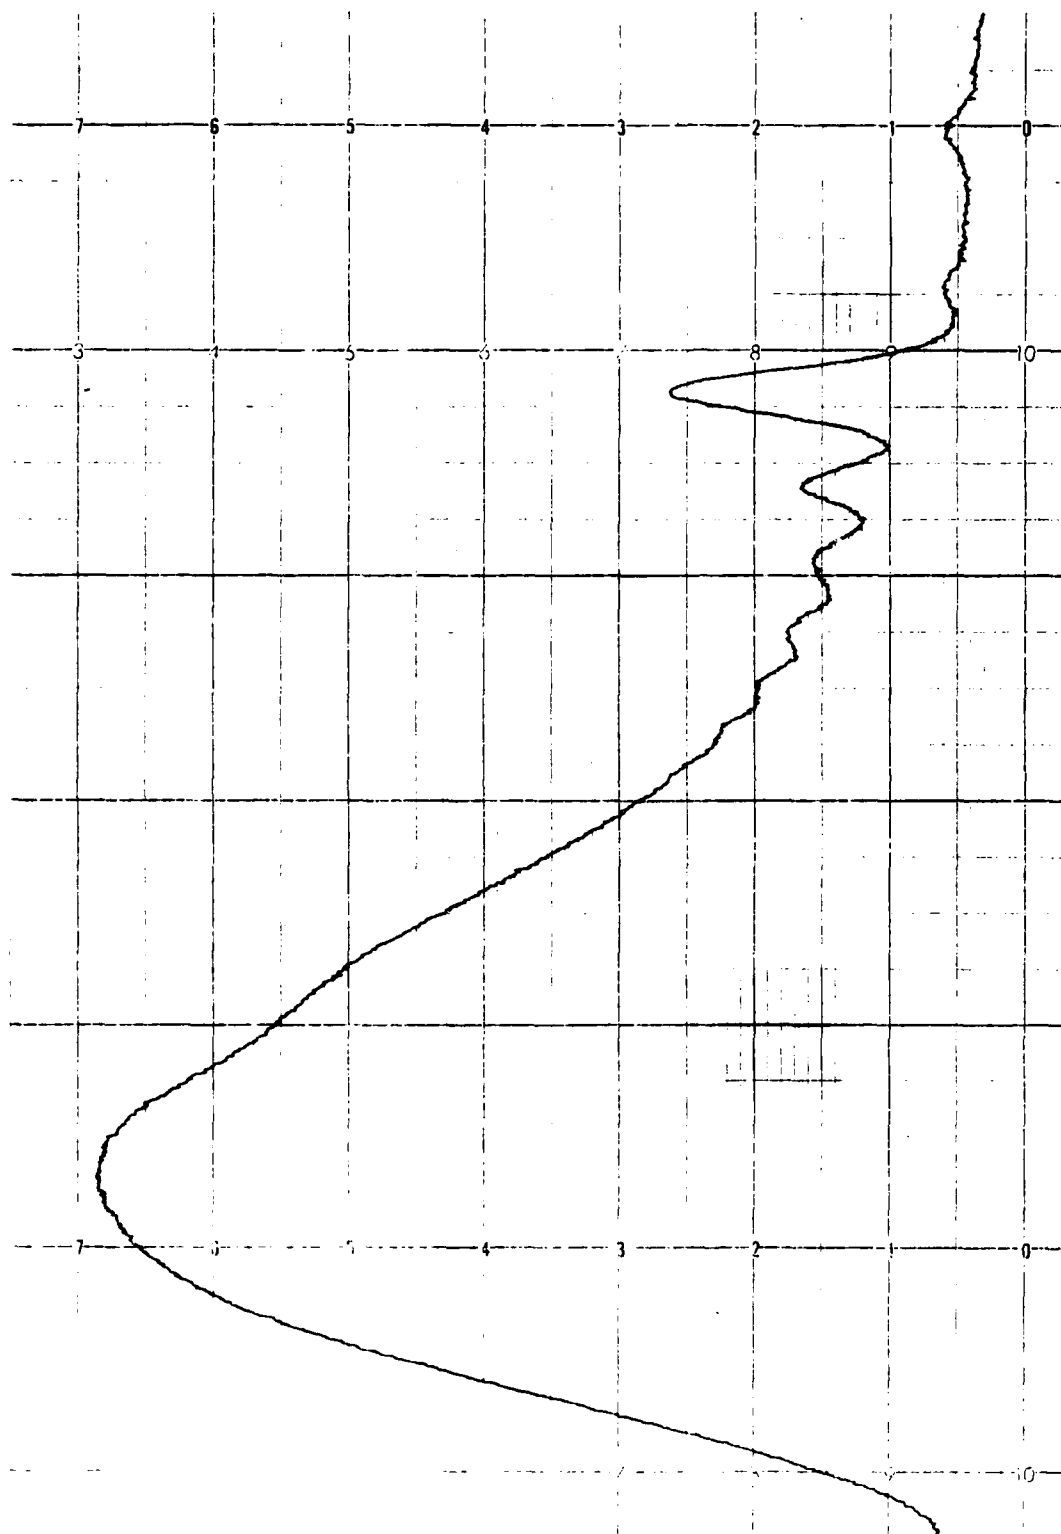


FIGURE 4. GPC OF POLYFORMAL OF  $\text{HOCH}_2(\text{CF}_2)_3\text{CH}_2\text{OH}$ ; CYCLIC FORMALS ARE NOT COMPLETELY REMOVED

Although this ring system is not strained and both cis- and trans-isomers are formed with almost equal ease in the carbocyclic ring system, the reactions tried so far were not successful.

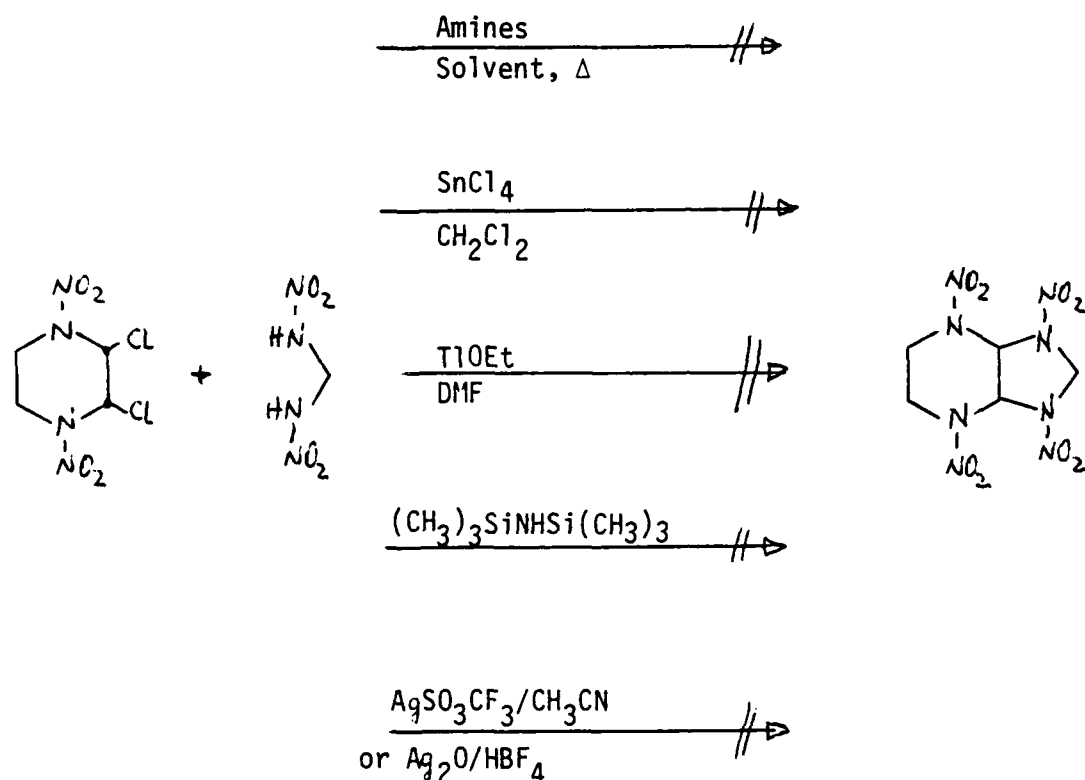

Reactions of 22c and 22d with  $\text{NH}_3$ , tert-butylamine, and urea also gave no isolable products. Under some conditions self-condensation products of 22 were obtained which were shown to be oxa-analogs of the desired polycyclic nitramines, an indication that such ring systems are stable.

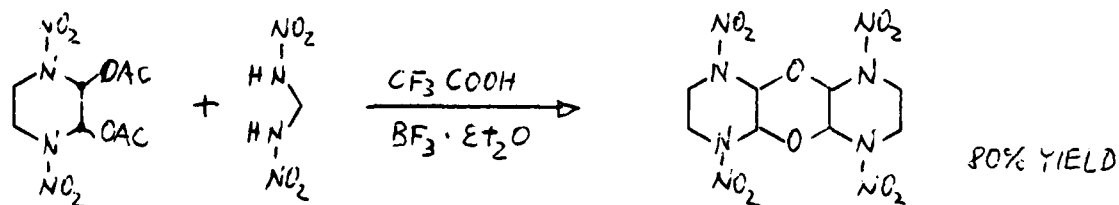



C1CN2C(=N1)N(C(=O)N)C2N(C(=O)N)

O=[N+]([O-])c1ccc2c(c1)[nH]c3cc([N+](=O)[O-])cc([N+](=O)[O-])c3n2

O=[N+]([O-])c1c([N+](=O)[O-])c2c([N+](=O)[O-])c3c2c1c([N+](=O)[O-])c3[N+](=O)[O-]

$$n=1: \rho_0(\text{CALC'D}) = 1.95$$



$$n=2: \rho_c (\text{CALC'D}) = 1.96$$

O=[N+]([O-])c1ccnc([N+](=O)[O-])c1Y
$$Y = \text{OAc} \text{ (22a)}, \text{CF}_3\overset{\text{O}}{\parallel}\text{C} \text{ (22b)},$$


Cl (22c), Br (22d)




Among the linear polycyclic nitramines whose synthesis we have pursued are the diaza- and tetrazabicyclooctanes 18 and 19. Some simple approaches

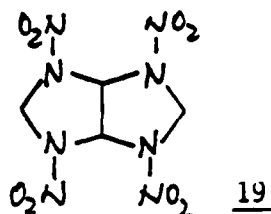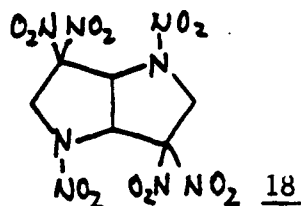

to the parent amine of 18 were tried and failed to give the expected product:


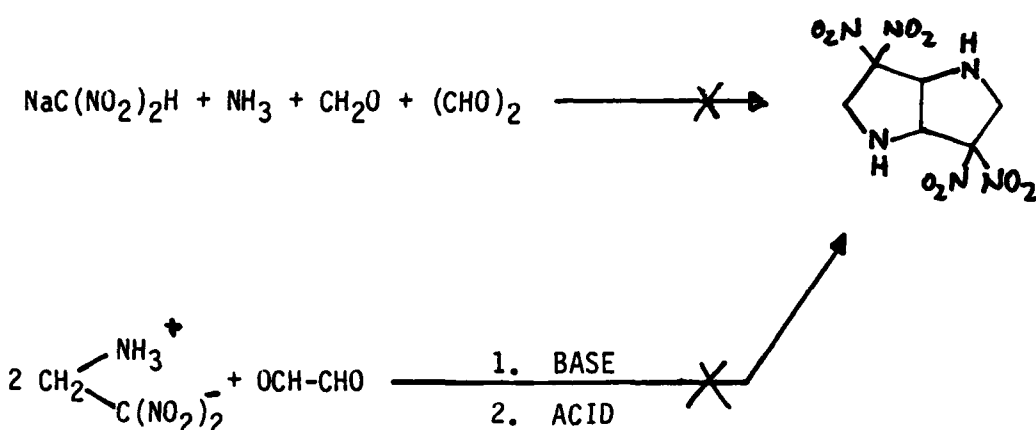


A more promising route starts with derivatives of the known dilactam 20. This compound can be brominated and alkylated to give 21. The chemistry of these diazabicyclooctanes is currently being investigated with a view toward synthesis of 18 and its dioxo derivative.

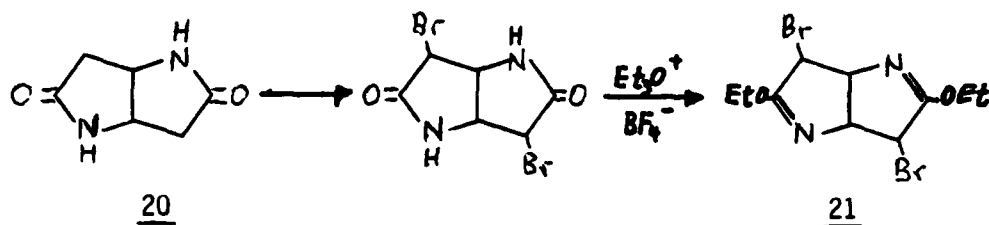


A few more attempts were made at the nitrolysis of the previously synthesized tetraacetyltetrazabicyclooctane to 19. Like all previous such attempts, they were unsuccessful.


1.  $\text{Br}_2$  1:1 OR EXCESS; DCE OR SULFOLANE;  
R.T. -  $60^\circ$   
→ RING DEGRADATION;  $\text{NH}_4\text{Br}$
2. T-BUTYL HYPOCHLORITE 1:2;  $\text{CH}_2\text{Cl}_2$ ;  
R.T., 24h  
→ DAPT SALT + OIL; NMR EVIDENCE FOR

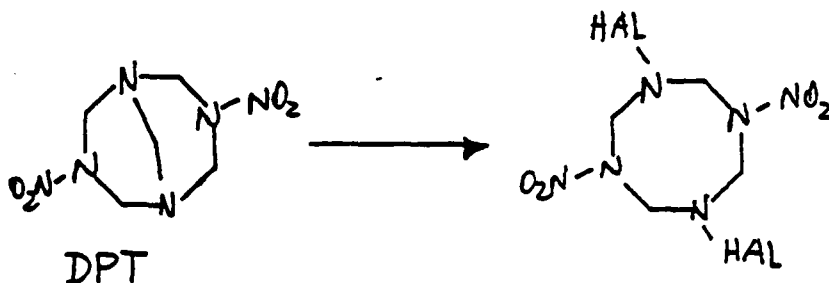


<u>REAGENT/CONDITIONS</u>	<u>RESULT</u>
BROMINE/SULFOLANE R.T. - $60^\circ$	ADDUCTS (?); DPT CAN BE REGENERATED
$\text{Br}_2$ /SILVER ACETATE; $\text{MeOAc}$ , R.T.	LITTLE REACTION
m-CHLOROPERBENZOIC ACID; $\text{MeOAc}$ , R.T.	PRODUCT FORMS DPT + GAS ON STANDING; NMR SIMILAR TO BROMINE ADDUCTS
DITTO, 20h REFLUX	SMALL AMOUNT UNIDENTIFIED SOLID; DPT; MIXTURE OF SOLUBLE PRODUCTS
$\text{PCl}_5$ /SULFOLANE, $\text{MeOAc}$ ; R.T.	ADDUCT FORMATION AND WATER-SOLUBLE PRODUCTS
CHLOROSUCCINIMIDE/DCE; REFLUX	NO REACTION
T-BUTYL HYPOCHLORITE/ SULFOLANE, $\text{MeOAc}$ ; $70^\circ$	PRODUCT MIXTURE WITH POSSIBLE $\text{H}-\text{C}=\text{N}$ SIGNAL IN NMR
CHLORINE; $\text{MeOAc}$ ; R.T.	HYGROSCOPIC SOLID : $\text{Cl}-\text{N} \begin{array}{c} \diagup \quad \diagdown \\ \text{N} \quad \text{N} \end{array} -\text{CH}_2\text{Cl} ?$
$\text{Cl}_2/\text{NaOAc}$ ; $\text{MeOAc}$ ; R.T.	PRODUCT WITH STRONG $\text{H}-\text{C}=\text{N}$ SIGNAL

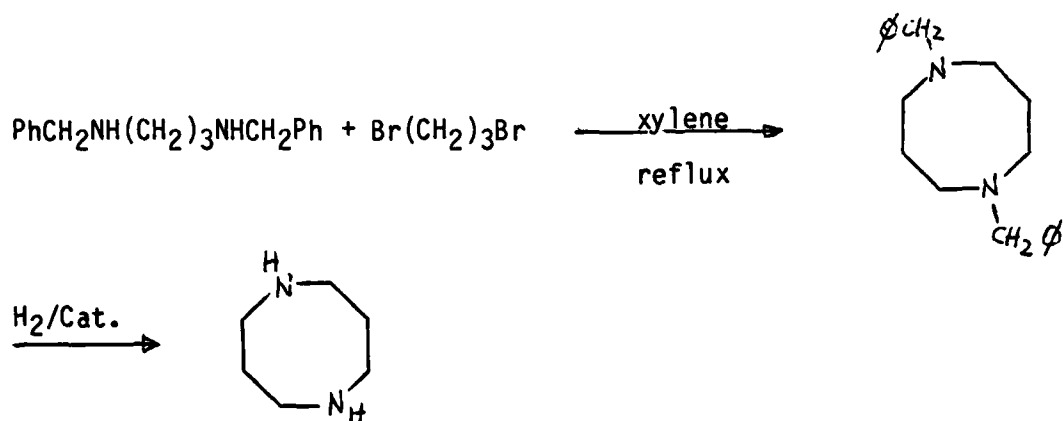


Attempts are also underway to synthesize diazacyclooctadiene directly by the two routes shown:


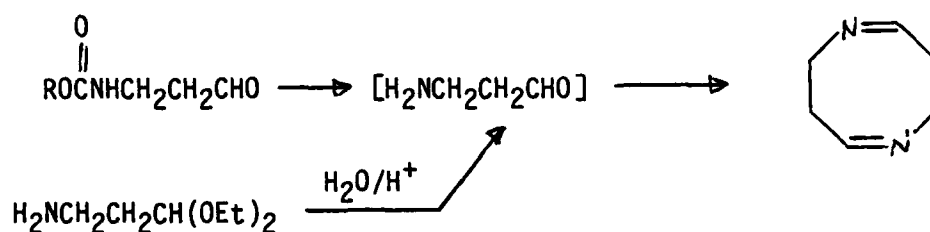


We have also prepared a quantity of the dihydroxydiazacyclooctane 16 by a known route and are studying its dehydration to the diene 17, another substrate of interest for transannular addition reactions.

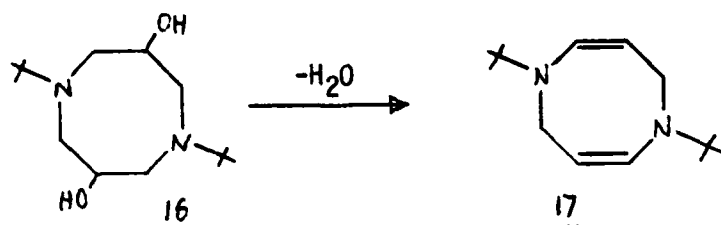


Attempts have also been initiated to prepare compounds 15 by halogenolysis or similar reactions of DAPT and DPT. In these reactions, which are tabulated below, NMR evidence has been obtained for formation of the desired -N-CH=N- moiety, but pure products have not yet been isolated.

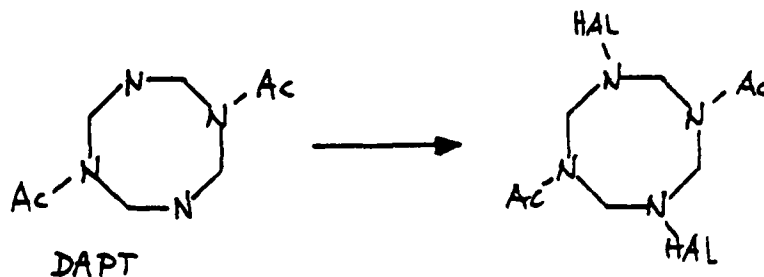

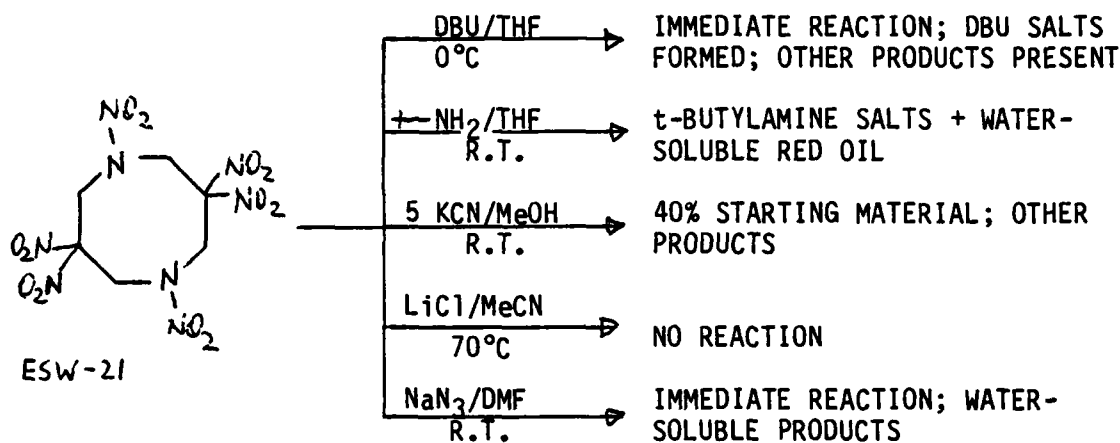

We plan to repeat some of these reactions at low temperature, if a suitable solvent can be found, in the hope that more tractable products will be formed.


Another possible route to 13 is elimination of HCl or HBr from N-haloamines such as 15. Such eliminations have been carried out with simple

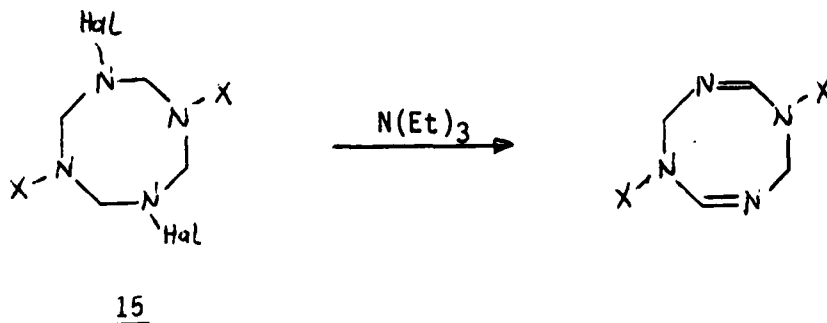

chloramines and occur quite readily. Since a milder base can be used for the first step, it may be possible to avoid the subsequent reactions which were observed with DMMD and HMX.


Again for the purpose of conducting model studies, the synthesis of 1,5-diazacyclooctane was initiated. This material will be chlorinated, and dehydrochlorination and transannular additions will be studied.

indicating multiple reactions. A similar result was obtained with DADN:

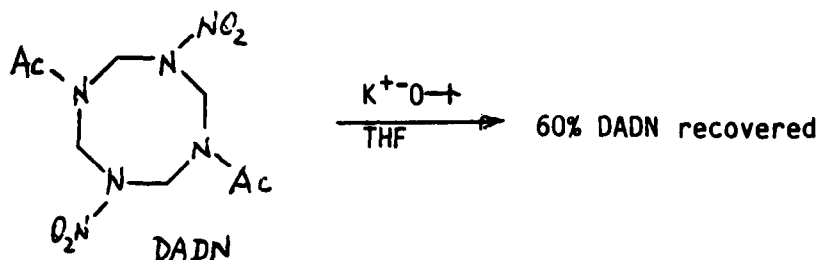


The above reactions were all quenched in D<sub>2</sub>O; the recovered starting materials showed no deuterium incorporation by NMR.

HMx was also reacted with several other bases and nucleophiles; in all cases a similar reaction pattern was observed (i.e., consumption of base, partial recovery of HMx; water soluble products, if any). It appears from these results that nitrous acid elimination from a methylene dinitramine unit is not a feasible approach to structure 13.

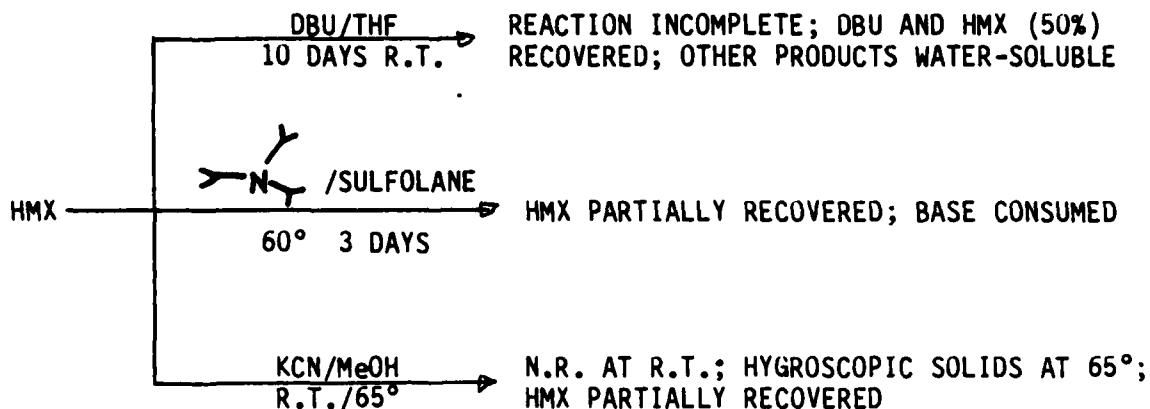



In contrast to the methylene dinitramines, 2,2-dinitroethyl nitramines such as ESW-21 were highly reactive with bases. A number of reactions which have been tried gave no isolable, well-defined products, however. In this case a possible complication is the reverse Mannich reaction which would lead to ring-opening and water-soluble dinitroalkane salts:

Since nitrous acid elimination from RDX had been reported earlier,<sup>6</sup> this reaction was studied with both acyclic and cyclic substrates to assess its

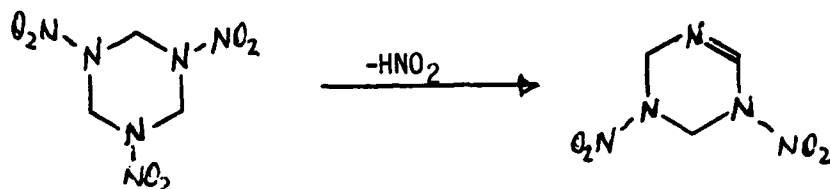



potential as a route to 13.

The reaction of DMMD with bases was studied as a simple model for the more complex reaction in a cyclic system. In view of Hoffsommer's results<sup>6</sup> it was surprising that DMMD did not react with sodium hydride in benzene, with butyl lithium in THF, or with lithium tetramethyl piperidide in THF. Reaction did occur, however, with potassium tert-butoxide:

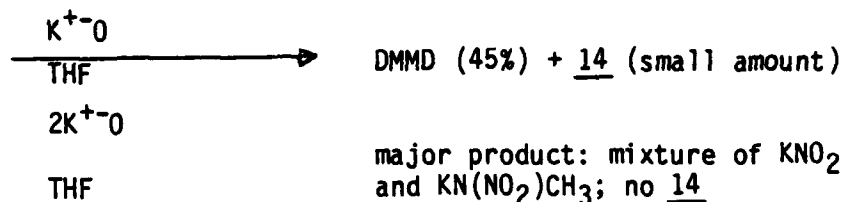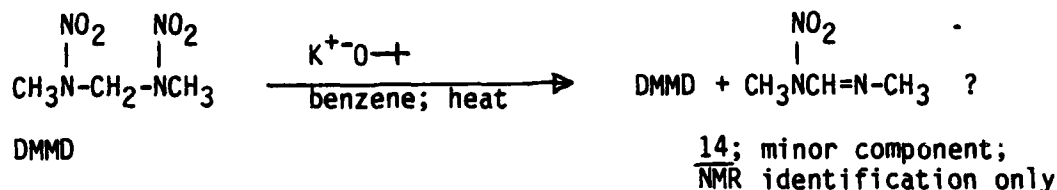


It appears that the desired reaction takes place but that 14 reacts more rapidly with base than the starting material. The nature of the second step is not known, but it could be a displacement reaction leading to the formation of potassium methyl nitramine, which was observed as a reaction product.

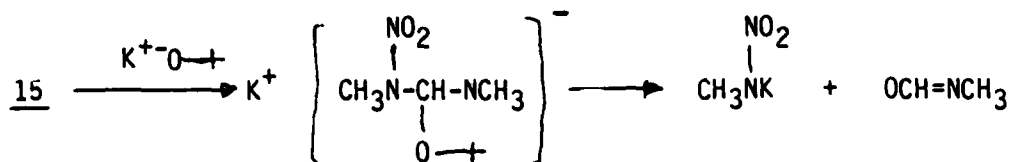

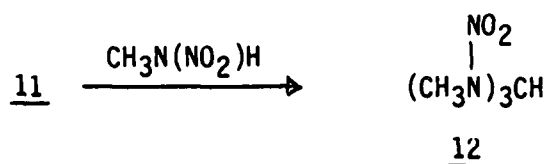




compound 8 should be stable also. The alkoxymethylene dinitramine structure of 11 should be stabilized by incorporation into the bicyclononane ring system.

The reactions leading to 10 and 11 were also carried out with ethylene dinitramine instead of methyl nitramine. It was hoped that formation of the 5-membered ring would provide a strong driving force for these reactions. However, this was not the case, and the desired products were not obtained. We currently have no convincing explanation for this unexpected finding.

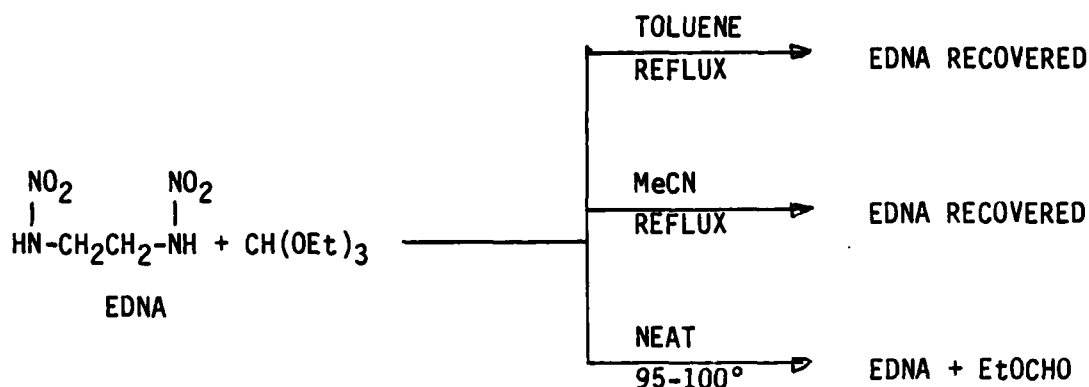


One synthetic approach to compounds 6 and 8 we decided to pursue involves the generation of the appropriate cyclooctadiene precursor and introduction of the hetero-atom bridge via a transannular addition reaction:

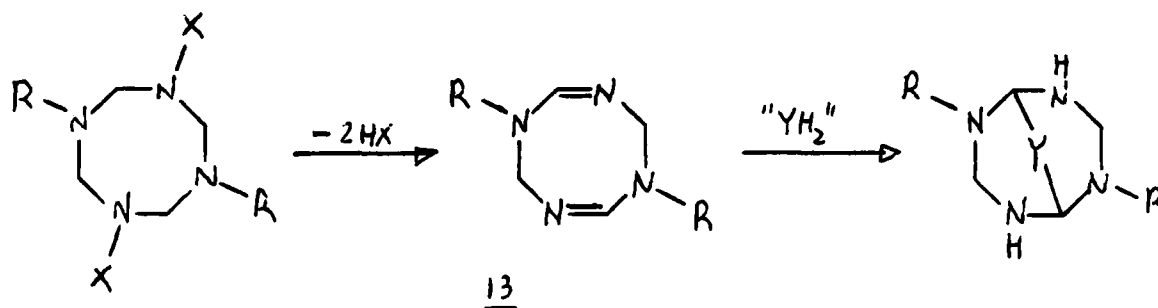

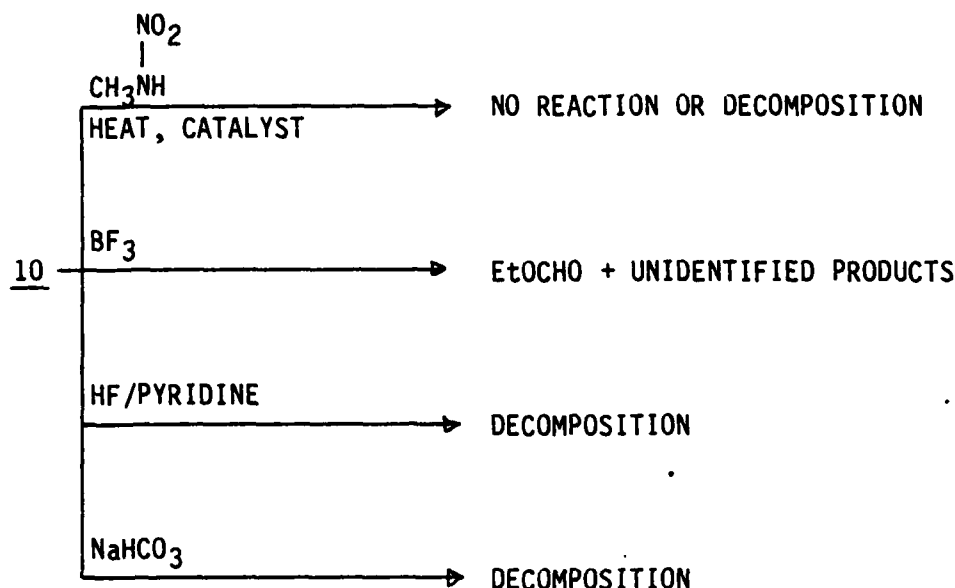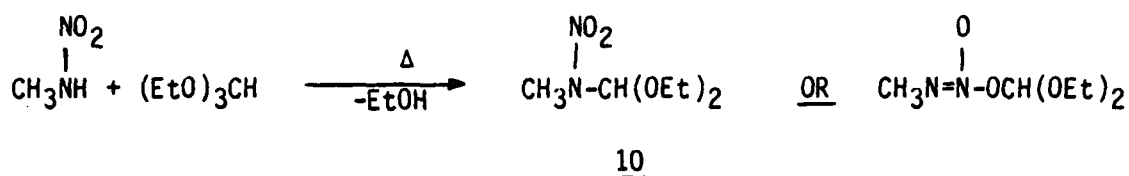

accomplished by the reaction of potassium methyl nitramine with dichloromethyl methyl ether in low yield. The structure of 11 was confirmed by a crystal

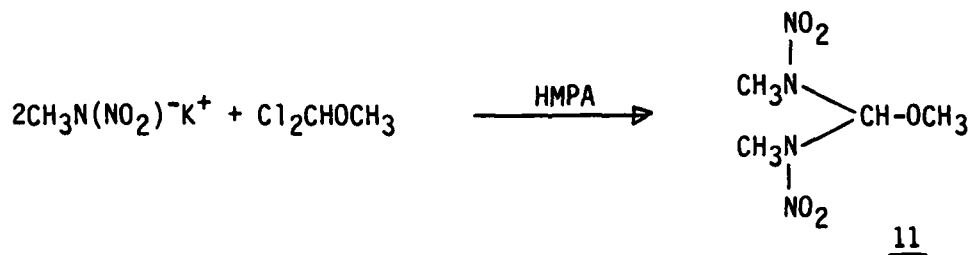


17%; MP 53-4°C (dec.)

structure determination (R. Gilardi, NRL), since an isomeric structure analogous to 10 was possible and not distinguishable by spectroscopic or analytical means. 11 is a model structure for 8, and to our knowledge is the first and only known hetero-substituted methylenedinitramine. 11 is not very stable and decomposes slightly above its melting point. As in the case of 10, further reaction with methyl nitramine to 12 was not successful, and 11 is sensitive to both acids and bases. The existence of 11 indicates that




The linear polycyclic compounds (g) and (h) are of interest also.

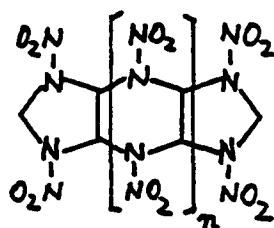

(g) : 1.95 g/cm<sup>3</sup>  
(h) : 1.96 g/cm<sup>3</sup>

This year's efforts have concentrated on two types of target compounds:  
(1) Heterobicyclononanes, and (2) linear polycyclic nitramines.

The heterobicyclononanes of interest are structures 6 - 9:

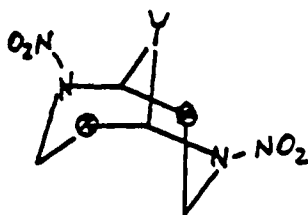

6: Y = N-NO<sub>2</sub>; = N-NO<sub>2</sub>;  $\rho_0$  (calc'd.) = 1.07 g/cm<sup>3</sup>

7: Y = N=NO<sub>2</sub>; = C(NO<sub>2</sub>)<sub>2</sub>

8: Y = O; = N-NO<sub>2</sub>;  $\rho_0$  (calc'd.) = 1.94 g/cm<sup>3</sup>

9: Y = O; = C(NO<sub>2</sub>)<sub>2</sub>

Because structures of this type are not known, the initial effort was to synthesize acyclic analogs in order to assess synthetic approaches and the stability of such compounds.

The reaction of methyl nitramine with ethyl orthoformate gave a mono-substitution product 10, but further reaction to 11 was not possible; 10 is a very reactive substance; all reactions tried led to degradation products. Since the structure of 10 (a liquid) is not fully established, this observation is of limited utility at present. The synthesis of 11 was

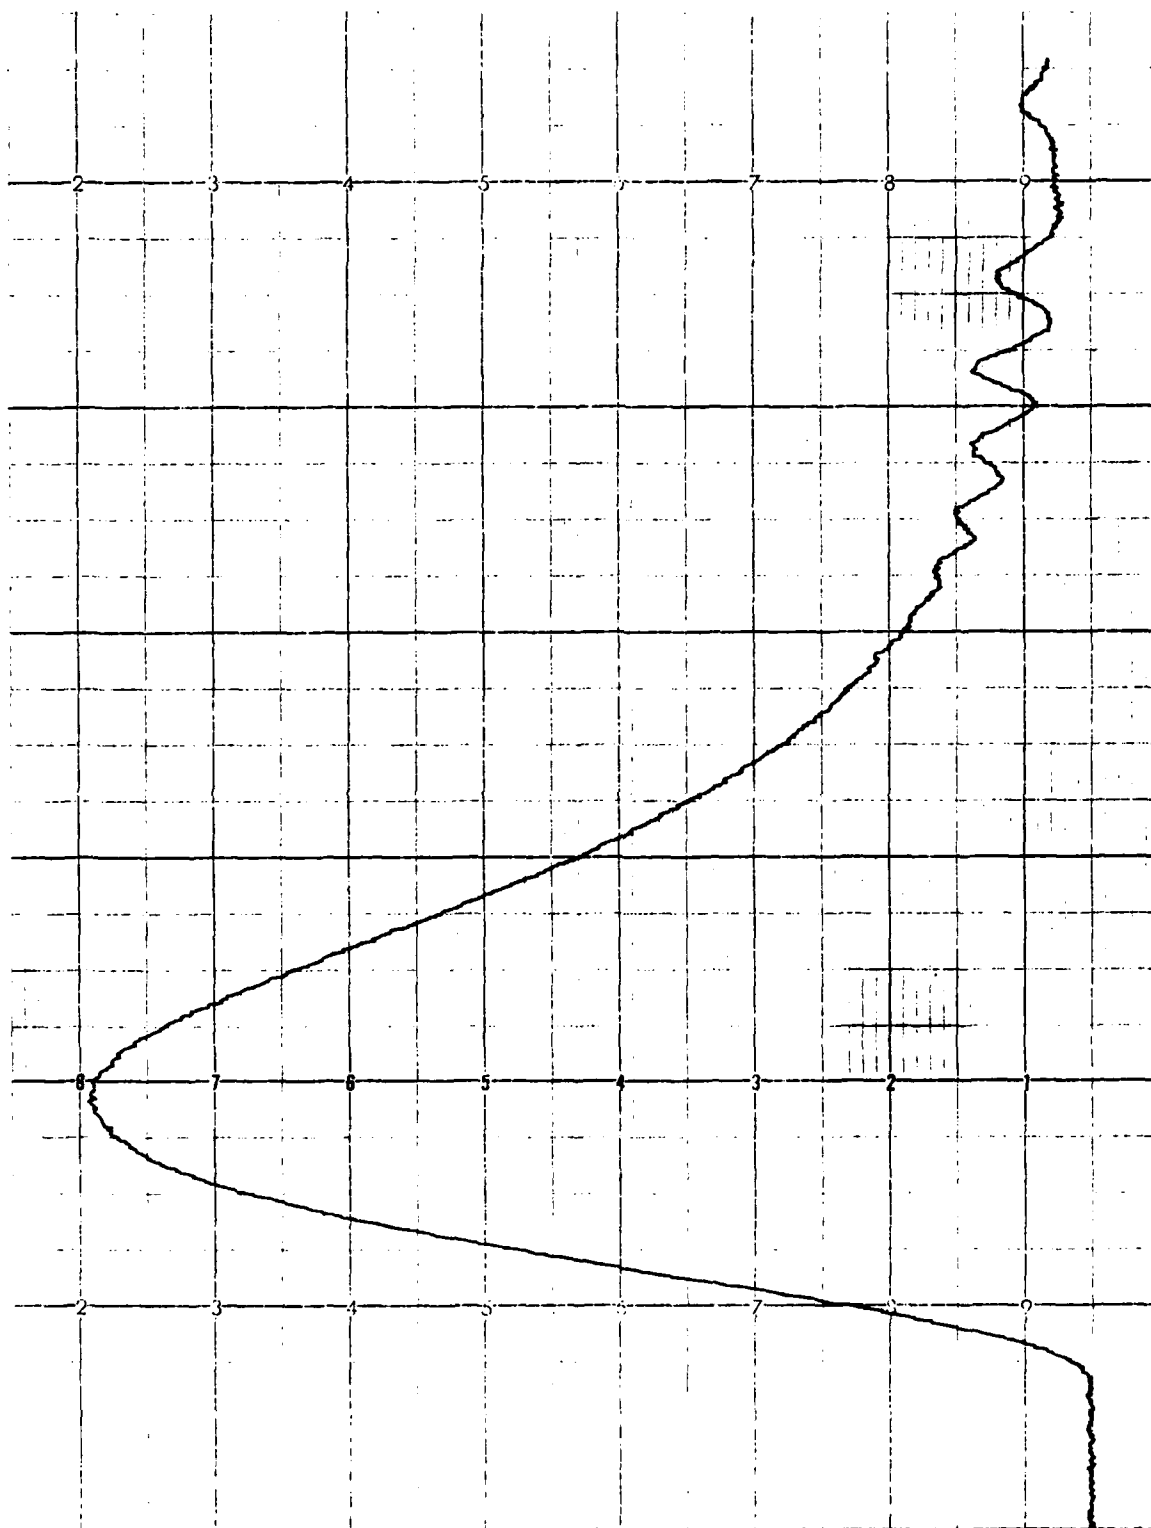


FIGURE 6. GPC OF POLYFORMAL OF  $\text{HOCH}_2(\text{CF}_2)_4\text{CH}_2\text{OH}$

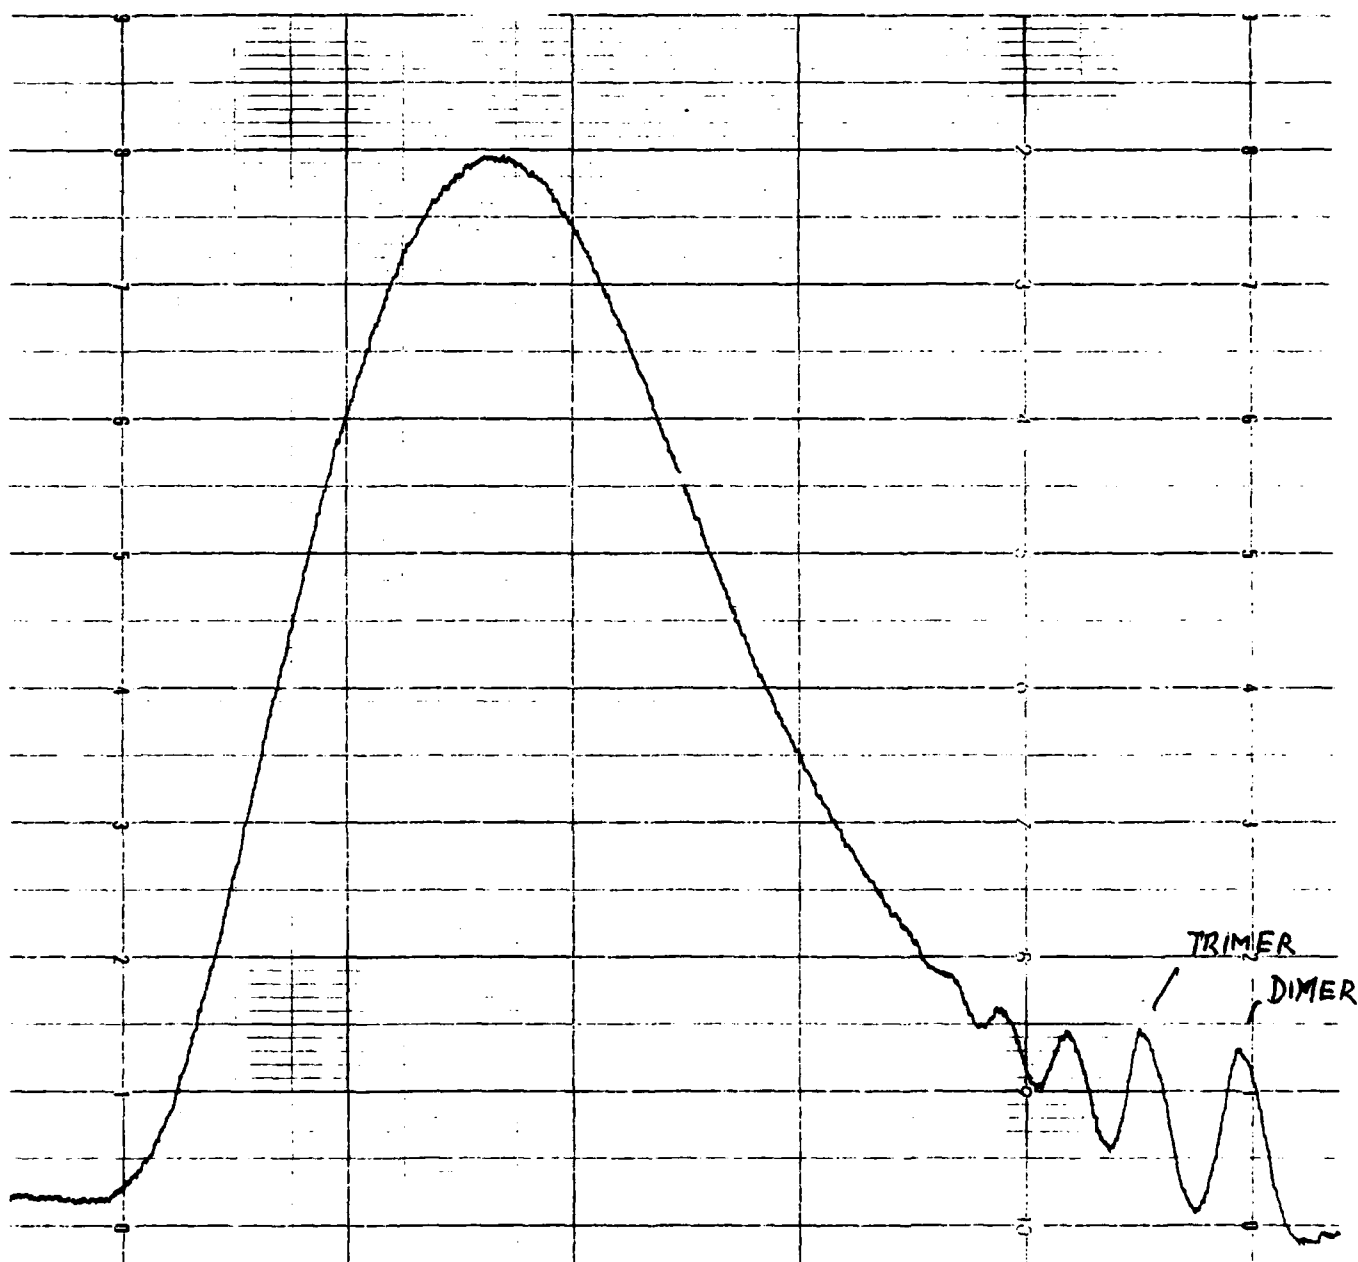



FIGURE 5. GPC OF POLYFORMAL OF  $\text{HOCH}_2(\text{CF}_2)_3\text{CH}_2\text{OH}$ ; IMPROVED PROCEDURE

Fig. 5 shows the GPC of a 25g sample of  $M_n$  3100 prepared by this procedure.


Diol 5 reacted with a slight excess of  $\text{CH}_2\text{O}$  under the same conditions as 4 to give mostly polymer ( $\approx 85\%$ ) plus a small amount of cyclic formal which was readily removed by heating to  $110\text{--}120^\circ\text{C}$  in vacuo. The GPC is shown in Fig. 6. Like the polymer from 4, this material is a viscous liquid at room temperature. The molecular weight ( $M_n$ ) was 6400. Attempts to reduce the molecular weight by reducing the formaldehyde: diol ratio were only moderately successful. When this ratio was reduced from 1.2:1 to 1:1, a  $M_n$  of 5300 was obtained. The polymer was shown to be difunctional by hydroxyl analysis and demonstration of curing. Gumstocks of this polymer with FEFO plasticizer are stable only up to a FEFO content of 50 weight percent.

#### SYNTHESIS OF POTENTIALLY DENSE NITRAMINES


As discussed previously,<sup>5</sup> the calculated densities of cyclic and polycyclic nitramines of the type (b) - (f) are sufficiently higher than that of HMX (a) to make such structures candidates for high energy-density explosives with predicted detonation pressures in the range of 420-470 Kbar. The first set of density values shown below are for the all-nitramines, whereas the numbers in the parentheses are for compounds in which half of the nitraza groups are replaced by gem-dinitro. Note the trend to higher densities with increasing number of rings in the molecule, and the increasing density difference between all-nitramine and mixed nitraza/gem dinitro compounds.

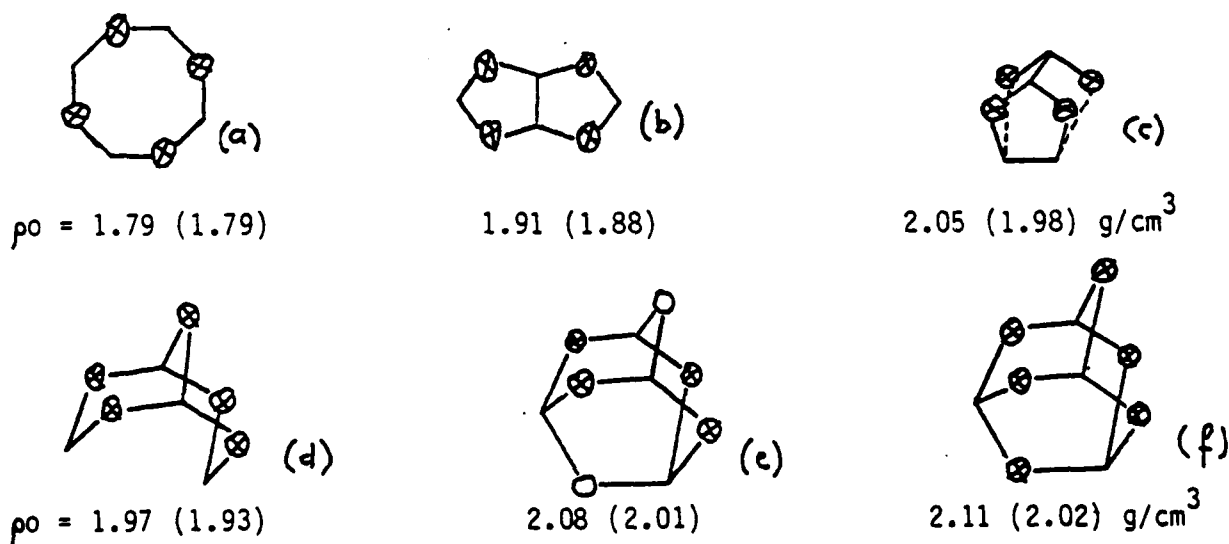


⊗ =  $\text{N-NO}_2$  or alternating  $\text{N-NO}_2/\text{C}(\text{NO}_2)_2$

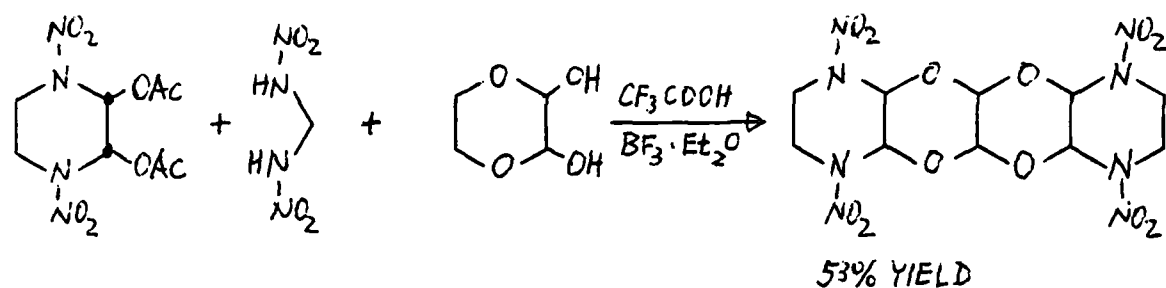

Although 22a and 22c were readily converted to the corresponding bromide and azide, attempts to obtain the fluoride from either 22c or 22d were not successful, possibly because of an interfering elimination reaction to the olefin (see below).

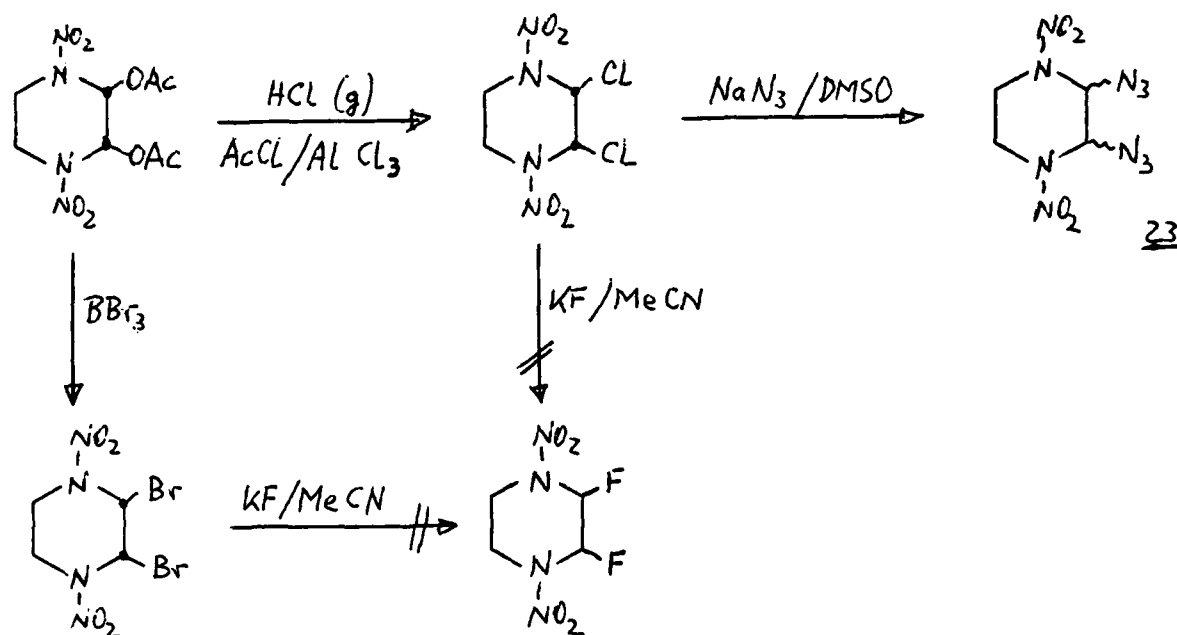


A number of attempts were made to reduce 23 to amines which could participate in condensation reactions to the desired ring systems. Direct hydrogenation gave no identifiable products, but reaction with phosphines gave  $N_2$  evolution

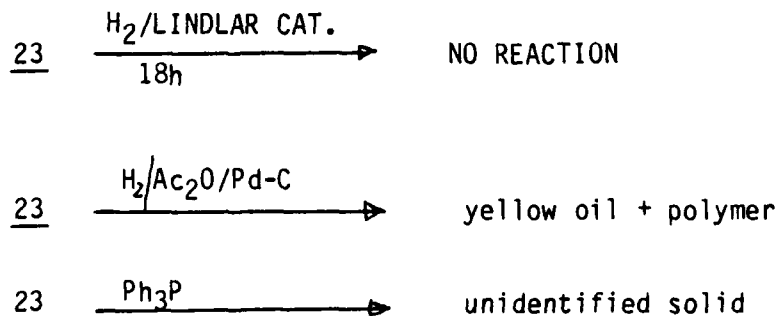





and stable solids, as yet unidentified. These investigations are continuing. An interesting observation was made in reactions of 22d with certain bases or nucleophiles where bromine elimination occurred to give the dinitrazaolefin 24.

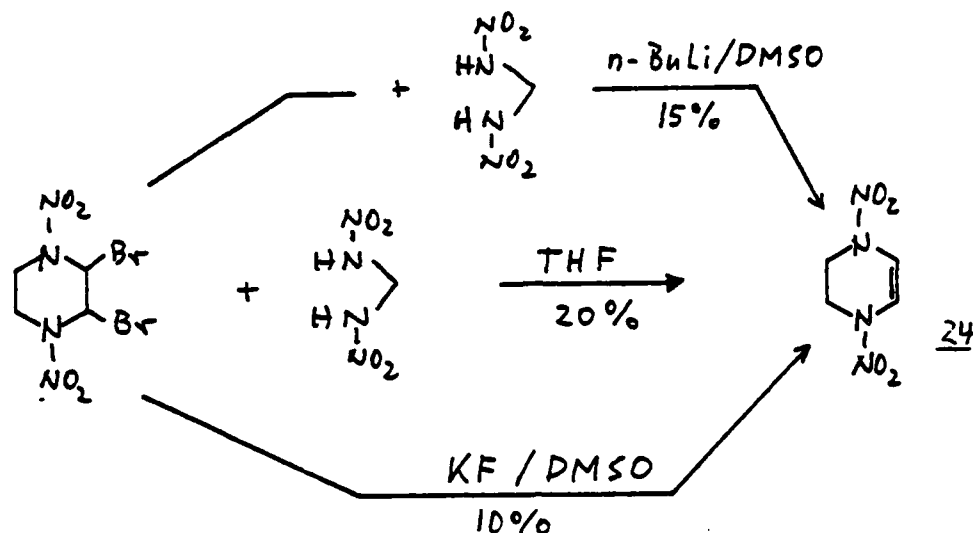

Better yields of 24 were obtained by treatment of 22d with triethyl phosphite or butyllithium in DMSO:

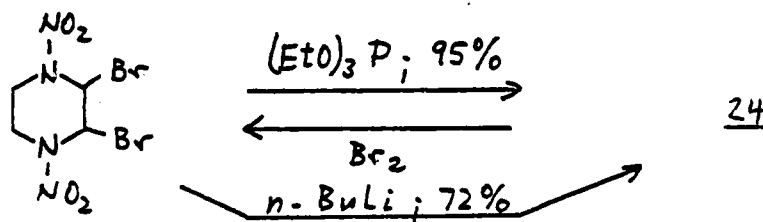


24 is to our knowledge the first reported dinitrazaolefin. It was hoped that it might be an active dienophile for reaction with azadienes which would be a route to the linear polycyclic ring systems discussed above:

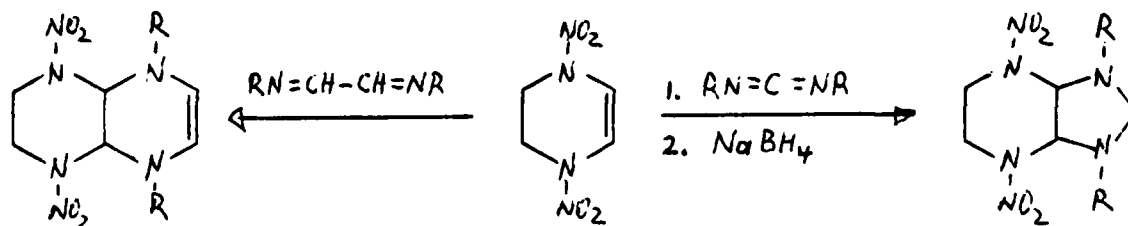


A preliminary investigation of the chemical properties of 24 indicates that the compound polymerizes on heating to about 60° and undergoes little reaction (Diels-Alder) with furan. These investigations are continuing.


Attempts were also made to synthesize the corresponding diene 26. The tetrabromide 25 was prepared from the known tetracetate<sup>7</sup>). A variety of known debrominating reactions were tried but none have been successful so

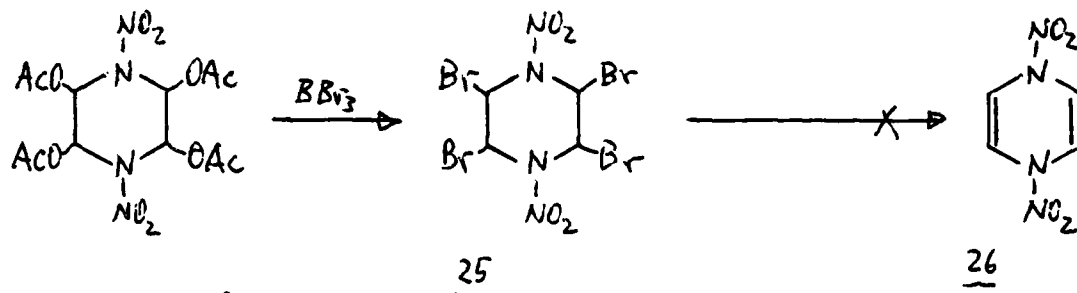

far due, probably, to the high reactivity or instability of this novel structure. Tetrabromide 25 was, however, converted into two highly reactive compounds 27 and 28. The diazide, 28, loses  $HNO_2$  and cyclizes into a heterocyclic ring system. The structure of this heterocycle, at first thought to be the bistriazolopyrazine 29, has now found by X-ray crystallographic analysis (Gilardi; NRL) to be the bistetrazolopyrazine 30.

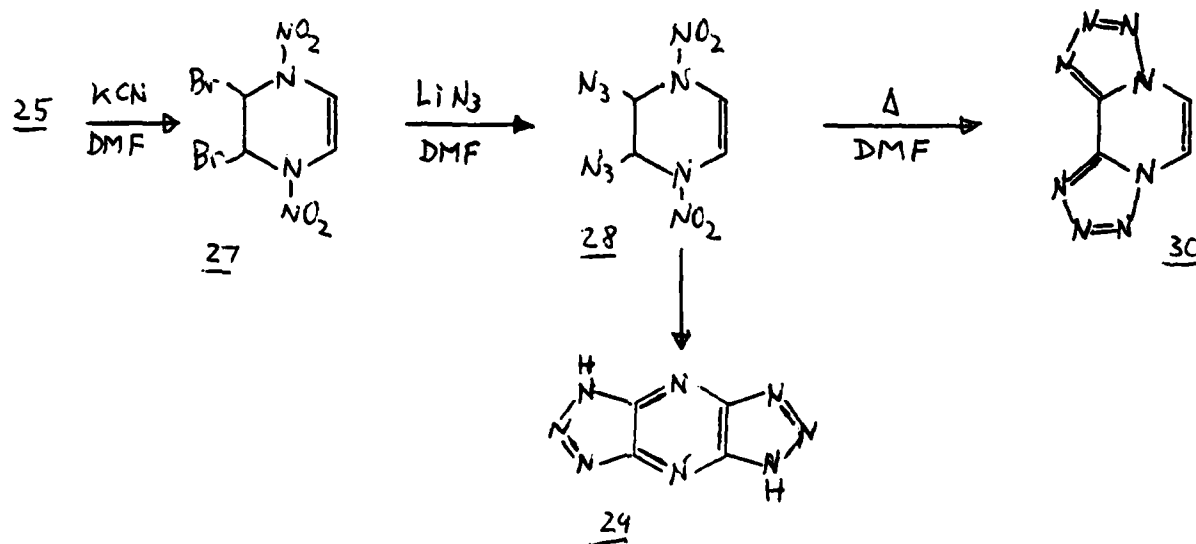

The tetranitratodinitramine 31 was prepared from the tetrahydroxy compound as a possible high-energy oxidizer. Although it crystallized in large colorless prisms, they became opaque within a few hours, and an X-ray density determination could not be carried out successfully. It appears that the physical change in the crystals is not due to surface hydrolysis, but to actual decomposition of the molecule.

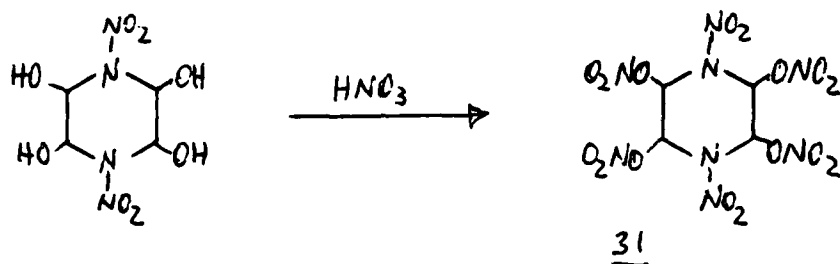



## Experimental Section

Melting points are uncorrected; temperatures are in °C unless noted otherwise. Microanalyses are by Galbraith Laboratories, Knoxville, Tennessee. NMR spectra were obtained on a Varian EM-390 spectrometer; chemical shifts are in ppm relative to TMS as internal standard.

Polyformal of 3,3,5,7,7-Pentanitro-5-azanonane-1,7-diol, 1; Modified Procedure.- In a 300 mL 3-neck flask 30g of the diol, 30 mL of dry (molecular sieves) sulfolane, and 2.097g of trioxane were mixed under a nitrogen blanket until homogeneous. 22.5 mL of  $\text{BF}_3$  etherate was added with ice-cooling and the mixture was stirred 24 h at room temperature. 200 mL of dichloromethane was added, and the solution was poured into a vigorously stirred mixture of 500 mL of water, 27g of  $\text{NaHCO}_3$ , and 12 mL of 30%  $\text{H}_2\text{O}_2$ . The reaction flask was washed with 50 mL of a 1:1 mixture of dichloromethane and methyl acetate which was combined with the main drowning mixture. After 3.5 h vigorous stirring, the phases were separated and the aqueous phase was washed with 50 mL of 1:1 dichloromethane/methyl acetate. The combined organic layers were freed from solvents on a rotary evaporator (1.5h/40°C). The residue was dissolved in 45 mL of warm methanol and the solution was poured slowly into a vigorously stirred mixture of 270 mL of water and 135 mL of methanol. Stirring was continued until the aqueous phase was only moderately turbid. The liquid phase was poured off and the remaining resin was triturated with water overnight, then dissolved in 300 mL of 1:1 dichloromethane/methyl acetate. The solution was dried ( $\text{MgSO}_4$ ) and stripped for 3-4 h/45°C. The residue was triturated with a mixture of 390 mL of dichloromethane and 240 mL of hexane for 72 h, the solvent was decanted and the residue stripped at 45°C for 6 h. Obtained was 25g polymer as a pale yellow powder. GPC analysis (Fig. 1) gave the following data (after exclusion of 8% of low molecular weight cyclic material):  $M_w = 3780$ ;  $M_n = 2860$ ; polydispersity = 1.32. The hydroxyl equivalent weight was determined by the NMR method <sup>1)</sup> as  $1740 \pm 0.7\%$ .

Curing of FEFO Solution of Polyformal of 1.- 1.11g of the above polymer was dissolved in 2.0g of FEFO (2,2,2-Fluorodinitroethyl formal) with warming at 50°C, followed by 0.02g each of N-methyl-4-nitroaniline and 2-nitrodiphenylamine. 0.002 mL of dibutyltin dilaurate was mixed in thoroughly, followed by 0.091g of PAPI-135. The mixture was degassed at 50°C for 0.5 h and was then cured at 50°C for 4 days to give a clear gumstock with good strength and excellent elongation.

3,3-Dinitropropyl Acetate from Potassium 3,3-Dinitropropanol.- 61.2g of Potassium 3,3-dinitropropanol was dissolved in 190 mL of ice-water. To this was added rapidly with stirring and cooling 18.9 mL of conc. sulfuric acid diluted to 63.1 mL by pouring on ice. After 1 h additional stirring in the melting ice-bath the phases were separated and the aqueous layer was saturated with NaCl and extracted with ether (4x100 mL). The dried ( $\text{MgSO}_4$ ) solution was concentrated on a rotary evaporator and the residue was taken up in 65 mL of dichloromethane. 65 mL of acetyl chloride was added with ice-cooling; the mixture was allowed to warm to room temperature and was then refluxed for 2 h. After cooling and drowning on ice, the phases were separated. NaCl was added to the aqueous phase which was extracted with four 100 mL portions of dichloromethane. Usual work-up gave 47.2g of 3,3-dinitropropyl acetate which was pure by <sup>1</sup>H NMR ( $\text{CDCl}_3$ ):  $\delta$  6.40 (t,1), 4.36 (t,2), 2.58 (overlapping triplets,2), 2.10 (s,3).

Polyformal of 3,5,5-Trinitro-3-azaheptane-1,7-diol,2.- A mixture of 1g of diol 2, 1 mL of dry sulfolane, and 0.1007g of trioxane was stirred until homogeneous. 0.3 mL of  $\text{BF}_3$  etherate was added with ice-cooling and the mixture was stirred at ambient temperature for 20 h. 10 mL of Dichloromethane was added and the solution was poured into a mixture of 0.36g of  $\text{NaHCO}_3$  and 30 mL of water and stirred 3 h with occasional addition of  $\text{NaHCO}_3$  to adjust the pH to 7. The phases were separated, the dichloromethane layer was dried ( $\text{MgSO}_4$ ), filtered, and stripped in vacuo to give the crude polyformal. This material was analyzed by GPC (Fig. 2) without further purification. When larger amounts of  $\text{BF}_3$  etherate (0.45 mL, 0.75 mL) were used with an otherwise identical procedure, the products contained larger proportions of low molecular weight cyclic formals.

4,4,6,6-Tetranitro-2,6-diaza-1,7-heptanedicarboxylic Acid,5 A solution of 22.8g (0.086 mol) of ethyl 3,5,5-trinitro-3-azapentanoate<sup>8</sup>, 185 mL of 50% aqueous methanol, 12.0g (0.086 mol) of ethyl glycine hydrochloride, and 7.2g of formalin (36%, 0.086 mol) was stirred at room temperature while 7.2g (0.086 mol) of  $\text{NaHCO}_3$  was added in small portions (15 mL additional methanol used to rinse walls of flask after this addition was complete). After 2 h the solution was extracted with dichloromethane and the extract concentrated on a rotary evaporator to an oil. Addition of this oil to a well-stirred and ice-cooled mixture of 51.5 mL of 90%  $\text{HNO}_3$  and 51.5 mL of conc.  $\text{H}_2\text{SO}_4$  was followed by slow heating of the resultant solution to 55-60°C. After 5 min at this temperature the solution was allowed to cool slowly to 20°C and then poured on ice. Extraction with dichloromethane followed by removal of solvent gave the diethyl ester of the title compound as an oil. This was mixed with 85 mL of acetic acid and 17 mL of conc.  $\text{HCl}$  and heated at 70°C overnight. Volatiles were removed in vacuo, the residue diluted with water, and the diacid extracted with ether. The dried ether solution was concentrated in vacuo and the residue triturated with 100 mL of dichloromethane until it was converted to a powder. The isolated solid (14.3g, 45%) had mp 173°C (dec.);  $^1\text{H}$  NMR (acetone- $d_6$ )  $\delta$  5.43 (s,4), 4.87 (s,4).

Anal. Calcd for  $\text{C}_7\text{H}_{10}\text{N}_6\text{O}_{12}$ : C, 22.71; H, 2.72; N, 22.70. Found: C, 22.48; H, 2.91; N, 22.41.

3,5,5,7-Tetranitro-3,7-diaza-1,9-nonanediol,3.- The above diacid (7.8g, 0.021 mol) was added to an ice-cooled  $\text{THF} \cdot \text{BH}_3$  solution (1M, 86 mL). After 24 h at 20°C the solution was poured into water and this solution extracted with ether. The dried ether solution was concentrated in vacuo to 8.4g of oil. A dichloromethane/methyl acetate (7:3) solution of the oil was filtered through silica gel and separate fractions were collected. The fractions which crystallized after evaporation of solvent were combined and recrystallized from dichloromethane/acetone to give 5.7g (79%) of diol 3. Material which was dried at 55°C in vacuo overnight and in the presence of  $\text{P}_2\text{O}_5$  had: mp 95-7°C;  $^1\text{H}$  NMR (acetone- $d_6$ )  $\delta$  5.42 (s,4), 4.06 (m,8).

Anal. Calcd for  $\text{C}_7\text{H}_{14}\text{N}_6\text{O}_{10}$ : C, 24.57; H, 4.12; N, 24.56. Found: C, 24.80; H, 4.01; N, 24.77.

Polyformal of 3,5,5,7-Tetranitro-3,7-diaza-1,9-nonanediol,3.- 1g of Diol 3, 1 mL of dry (sieves) sulfolane, and 0.0789g of trioxane were mixed under a nitrogen blanket until homogeneous. The mixture was cooled in an ice-bath and 0.30 mL of  $\text{BF}_3$  etherate was added dropwise with stirring. After 24 h stirring at room temperature, the mixture was diluted with 10 mL of dichloromethane and poured into 30 mL water containing 0.4g of  $\text{NaHCO}_3$  and 0.4 mL of 30%  $\text{H}_2\text{O}_2$  which

was stirred. The reaction flask was rinsed with 10 mL of 1:1 dichloromethane/methyl acetate, and the combined drowning mixture was stirred vigorously for about 3 h until the organic solvents had evaporated. The solids were filtered off, washed with water, then triturated with water for 1 h, filtered and dried in air to give 0.95g of a white powder. GPC analysis (Fig. 3) gave the following data (after exclusion of 1.87% of low molecular weight cyclic material):  $M_w = 2977$ ;  $M_n = 1943$ ; polydispersity = 1.53.

Curing of FEFO Solution of Polyformal of 3.- 1.57g of polymer and 4.5g of FEFO were mixed by heating to 75°C. At 60°C, 0.0036g of dibutyltin dilaurate were mixed in followed by 0.197g of PAPI-135. The mixture was degassed at 60°C for 0.5 h, then cured 3 days at 60°C and 2 days at 50°C.

Polyformal of 2,2,3,3,4,4-Hexafluoropentane-1,5-diol,4; Direct Method.-

A homogeneous mixture of 160.9g of diol and 144.8 mL of 80% sulfuric acid was cooled in an ice-bath while 130 mL of dry dichloromethane and a solution of 27.6g of paraformaldehyde in 100.6 mL of 90% sulfuric acid were added (the latter dropwise). The mixture was stirred vigorously overnight at ambient temperature, then poured onto 1200g of ice (the flask was rinsed with a small amount of ice-water). 1200 mL of ether and 150 mL of 30% hydrogen peroxide were added, and the mixture was stirred vigorously for 1 h. The phases were separated and the ether layer was washed with 1200 mL of 5% KOH solution + 75 mL of 30% hydrogen peroxide, then with 700 mL of 2.5% KOH solution and with 700 mL of water, adding sodium chloride as necessary for phase separation. The ether solution was dried over Drierite with vigorous stirring, filtered through a "fine" sintered glass funnel and stripped in vacuo. Low molecular weight contaminants were removed by heating at 120-130°C/0.1 Torr overnight while the viscous liquid was being stirred slowly. The principal volatile products are unreacted 4 and 5,5,6,6,7,7-hexafluorodioxocane which can be collected in cold traps. The polymer yield was 67.7g; the GPC is shown in Fig. 4. This material had  $M_n = 4046$ ,  $M_w = 7584$ , polydispersity 1.87. The hydroxyl equivalent weight was determined using the NMR method<sup>1)</sup> with trifluoroacetic anhydride and was found to be 2098. The sample contained about 5% of cyclic formals which were subtracted from the chromatogram prior to calculation of the molecular weight.

5,5,6,6,7,7-Hexafluoro-1,3-dioxocane.- 100g (0.47 mole) of 2,2,3,3,4,4-Hexafluoropentanediol were added to a solution of 20g (0.67 mole) of trioxane dissolved in dry  $\text{CH}_2\text{Cl}_2$ . While stirring, 40 mL of trifluoromethanesulphonic acid were added at a moderate rate. The reaction mixture was then stirred at room temperature (~20°C) for 90 minutes, after which time 100 mL of water were added with cooling to dilute the trifluoromethanesulphonic acid. The  $\text{CH}_2\text{Cl}_2$  solution was washed with a dilute basic aqueous hydrogen peroxide solution (3%  $\text{H}_2\text{O}_2$ , 10% KOH) and brine, dried, and filtered. Removal of the  $\text{CH}_2\text{Cl}_2$  by rotary evaporation yielded a quantitative amount of the crude product as a viscous oil. Distillation gave 88g (83%) of pure 1,3-dioxo-5,5,6,6,7,7-hexafluorocyclooctane, b.p. 165-167°C, m.p. 24-25°C, density 1.584g/cm<sup>3</sup>.

Polymerization of 5,5,6,6,7,7-Hexafluoro-1,3-dioxocane.- 2.8g (13.21 mmol) of Hexafluoropentanediol (dried) were dissolved into 34.42g (153.66 mmol) of cyclic formal at 60°C. While stirring, 1.0 mL (11.307 mmol) of triflic acid was added in 100 $\mu$ l increments over the period of 1 h. The stoppered reaction mixture was then allowed to stand at 60° for 24 h, after which time 250 mL dichloroethane were added to dissolve the mass. The solution was washed twice

with 10 mL of 30%  $\text{H}_2\text{O}_2$  + 115 mL of 10% aqueous NaOH + 125 mL of brine and twice with brine. The dichloroethane solution was then passed through Whatman 1PS filter paper and most of the solvent was removed by rotary evaporation. The residue was subjected to high vacuum at  $140^\circ$  for several hours. Recovered polymer weighed 26.95g (72.5%). GPC analysis gave the following results:  $M_n = 3100$ ,  $M_w = 7000$ ,  $M_w/M_n = 2.14$ ;  $M_n$  (calculated) = 2800. Equivalent weight (g of polymer per OH group) was measured by the nuclear magnetic resonance spectrometric technique<sup>1)</sup> using trifluoroacetic anhydride to be 1537.

Curing of FEFO Solution of Polyformal of 4.- 0.88g of Polymer and 2.64g of FEFO were mixed at  $60^\circ\text{C}$  until homogeneous. 0.001g of Dibutyltin dilaurate was added via a microliter syringe and mixed in, followed by 0.072g of PAPI-135 and again thorough mixing. The mixture was degassed at  $50^\circ\text{C}$  for 0.5 h and cured at  $50^\circ\text{C}$  for 4 days.

Polyformal of 2,2,3,3,4,4,5,5-Octafluorohexanediol, 5.- 3.98 of Diol 5 was dissolved in 2.9 mL 80% sulfuric acid. the solution was stirred and cooled in an ice-bath and 2.6 mL of dichloromethane was added, followed by a solution of 0.456 g of paraformaldehyde in 2 mL of 90% sulfuric acid. After stirring 24 h at room temperature the mixture was poured over 30g of ice, 30 mL of ether and 3.75 mL of 30%  $\text{H}_2\text{O}_2$  were added, and the mixture was stirred 1 h. The polymer was isolated and purified as described above for the polyformal of 4. Obtained was 3.4g of a resin (81%) which was analyzed by GPC (Fig. 6):  $M_n = 5400$ ;  $M_w = 10,700$ ; polydispersity = 1.98.

Curing of FEFO Solution of Polyformal of 5.- The above polymer was miscible with FEFO at  $25^\circ\text{C}$  in ratios of 1:1 and 1:1.5. 7.35g of a 1:1.5 polymer-FEFO mixture was mixed with 0.005 mL of dibutyltin dilaurate and 0.157g of PAPI-135. The mixture was degassed at  $60^\circ$  for 0.5 h and was then cured at  $60^\circ\text{C}$  for 3 days and at  $50^\circ\text{C}$  for 2 days. The gumstock was homogeneous at  $50^\circ\text{C}$  but exuded some FEFO after storing at room temperature.

Methyl Diethoxymethylnitramine, 10.- 6.6 mL (40 mmol) of triethylorthoformate and 3.04g (40 mmol) of methylnitramine were mixed with 100 mL of toluene. Toluene was distilled off until the residual volume was 20 mL. The mixture was further concentrated at room temperature on a rotary evaporator and finally at 0.5 Torr. The resulting liquid was distilled at 0.4 Torr and  $80^\circ\text{C}$  pot temperature. Three fractions of 1, 2, and 1 mL were collected at  $56^\circ\text{C}$ . The middle fraction had the best purity but still contained about 15% methylnitramine. All attempts at further purification of this material were unsuccessful.  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  1.28 (t, 6H), 3.23 (s, 3H + methylnitramine increment), 3.73 (m, 4H), 6.56 (s, 1H).

3-Methoxy-2,4-dinitro-2,4-diazapentane, 11.- 2.0g (0.0175 mol) of Potassium methylnitramine in 10 mL of hexamethyl phosphoramide (distilled from  $\text{CaH}_2$ ) was cooled in an ice-bath and 0.8 mL (0.00875 mol) dichloromethyl methyl ether was added in 0.1 mL portions at 1 minute intervals. After 15 min. stirring the ice-bath was removed and stirring was continued for 1 h. The mixture was poured into 50 mL of ether and was then washed with 4 x 20 mL of water and with 20 mL of brine. Drying ( $\text{MgSO}_4$ ) and stripping gave 0.288g (17.0%) crude product which solidified upon storage at  $-10^\circ\text{C}$ . The sample was purified by sublimation at  $50^\circ\text{C}/0.05$  Torr; melting point  $51.7$ - $53.7^\circ\text{C}$ .  $^1\text{H}$  NMR ( $\text{CDCl}_3$ ):  $\delta$  3.33 (s, 6H), 3.63 (s, 3H), 7.53 (s, 1H).

Anal. Calcd for  $C_4H_{10}N_4O_5$ : C, 24.75; H, 5.19; N, 28.86. Found: C, 24.50; H, 5.14; N, 28.77%.

Reaction of 2,4-Dinitro-2,4-diazapentane (DMMD) with Potassium-t-butoxide.- 0.26g (1.38 mmol) of DMMD was dissolved in 10 mL of ether and 4 mL of tetrahydrofuran and 0.17g (1.38 mmol) of potassium-t-butoxide was added. The mixture was stirred for 3 h. NMR analysis showed that no reaction had occurred. The ether was distilled off and 10 mL of benzene was added. The mixture was refluxed 15 min. during which time dissolution and formation of a precipitate were observed. After cooling, the mixture was filtered through a column of celite and freed of solvent in a rotary evaporator.  $^1H$  NMR ( $CDCl_3$ ):  $\delta$  3.41 (two s, barely resolved), 3.67 (s), 5.69 (s), 9.02 (2s, barely resolved); the signals at 3.67 and 5.69 ppm are due mainly to DMMD; the signals at 3.41 and 9.02 ppm (ratio ~3:1) may be due to  $CH_3N=CH-$  while the missing- $N(NO_2)CH_3$  signal would overlap with the methyl signal of DMMD.

2,3-Dichloro-1,4-dinitropiperazine (22c).- To a stirred solution of 2,3-diacetoxy-1,4-dinitropiperazine (5.84g, 20 mmol) in acetyl chloride (40 mL) at room temperature was added aluminum chloride (3.0g, 22.5 mmol) in 0.5g portions over 45 min. Some of the aluminum chloride coagulated, and was broken-up with a glass rod. After 4 h the mixture was poured into 300 mL of ice and water and filtered to yield 4.25g (86.7%) of white solid: MP 143-146°C.

Similarly, 2,3-diazido-1,4-dinitropiperazine reacted with aluminum chloride in acetylchloride, with gas evolution ( $N_2$ ) to give the dichloride in 78% yield.

2,3-Dibromo-1,4-dinitropiperazine (22d).- To a stirred solution of 2,3-diacetoxy-1,4-dinitropiperazine (2.92g, 10 mmol) in  $CH_2Cl_2$  (50 mL), cooled in ice, was added boron tribromide (20 mL of 1.0M in  $CH_2Cl_2$ ). The ice bath was removed and stirring was continued for 1 h. The mixture was then diluted with  $CH_2Cl_2$  (50 mL), washed with water (2 x 25 mL), 5%  $NaHCO_3$  (2 x 30 mL), dried ( $MgSO_4$ ), and evaporated to give a white solid. Trituration with hexane, and filtering yielded 3.03g (90.7%): MP 130-131°C (dec). The analytical sample, of same MP was recrystallized from benzene-isopropyl ether.  $^1H$  NMR ( $CD_2Cl_2$ ):  $\delta$  3.77 and 4.70 (d, 4H,  $CH_2$ , J = 10Hz), 7.20 (s, 2H, CH) ppm; mass spectrum (CI,  $CH_4$ ) m/z 83 (100), 253 (60), 255 (M+1-HBr, Br = 81, 58) 333 (6), 335 (12) 337 (M+1, Br = 81, 5), 365 (M+29, 1.4)

Anal. Calcd for  $C_4H_6Br_2N_4O_4$ : C, 14.39; H, 1.81; N, 16.78; Br, 47.86. Found: C, 14.40; H, 1.72; N, 16.76; Br, 47.51.

2,3-Diazido-1,4-dinitropiperazine (23).- A solution of 2,3-dichloro-1,4-dinitropiperazine (2.45g, 10 mmol) and sodium azide (2.60g, 40 mmol) in dimethyl sulfoxide (60 mL) was stirred at room temperature for 24 h. The mixture was then poured into ice and water (250 mL) and the solid filtered to yield 1.56g (60.5%) of white solid: MP 107-110°C. Recrystallization from benzene-hexane gave colorless, flat needles: MP 110-112°C; IR (KBr) 2150 (sh) $cm^{-1}$ , and 2120, 1570, 1290;  $^1H$  NMR ( $CD_2Cl_2$ ):  $\delta$  3.89 and 4.50 (d, 4H,  $CH_2$ , J = 9Hz), 6.50 (s, 2H, CH) ppm.

Anal. Calcd for  $C_4H_6N_{10}O_4$ : C, 18.61; H, 2.34; N, 54.26. Found: C, 18.86; H, 2.37; N, 54.32.

1,4,6,9-Tetranitro-1,4,6,9-tetraaza-5,10-dioxaperhydroanthracene and 1,4,7,10-tetranitro-1,4,7,10-tetraaza-5,6,11,12-tetraoxaperhydronaphthacene.-

A mixture of 2,3-diacetoxy-1,4-dinitropiperazine (5.84g, 20 mmol), methylenedinitramine (2.72g, 20 mmol) and trifluoroacetic acid (200 mL) was heated to 60°C to dissolve the solids and then cooled to room temperature. Boron trifluoride etherate (3 mL, 3.46g, 24.4 mmol) was added and the mixture stirred for 18 h. The precipitate was filtered to give the perhydroanthracene (2.95g, 77.4%) as a white solid: MP 289°C (rapid dec). The solid was dissolved in hot DMF (100 mL) and diluted with ethanol (100 mL). Cooling and filtering gave the pure product: MP 292°C (dec); <sup>1</sup>H NMR (Me<sub>2</sub>SO-d<sub>6</sub>): δ 4.35 (m, 8H, CH<sub>2</sub>), 6.49 (s, 4H, CH); mass spectrum (CI, CH<sub>4</sub>) m/z 99 (100), 197 (30), 381 (M+1, 0.7), 410 (M+NO, 1.1), 421 (M+41, 0.33).

Anal. Calcd for C<sub>8</sub>H<sub>12</sub>N<sub>8</sub>O<sub>10</sub>: C, 25.27; H, 3.18; N, 29.47. Found: C, 25.40; H, 3.26; N, 29.30.

The DMF-ethanol filtrate from the above recrystallization was diluted with isopropyl ether (200 mL) and cooled in a refrigerator overnight to deposit 90mg of white solid. This product, upon heating in a capillary MP tube did not exhibit the rapid decomposition noted above for the perhydroanthracene, but slowly carbonized above 300°C. Spectroscopic and elemental analysis showed this to be the perhydronaphthacene. <sup>1</sup>H NMR showed a pair of multiplets centered at δ 3.96 and 4.43 (8H, CH<sub>2</sub>), 5.64 (s, 2H, OCHO), 6.75 (s, 4H, NCHO); mass spectrum (CI, CH<sub>4</sub>) m/z 99 (100), 439 (M+1, 1.2) 467 (M+29, 1.2), 479 (M+41, 0.25).

Anal. Calcd for C<sub>10</sub>H<sub>14</sub>N<sub>8</sub>O<sub>12</sub>: C, 27.40; H, 3.22; N, 25.57. Found: C, 27.42; H, 3.19; N, 25.62

1,4,7,10-Tetranitro-1,4,7,10-tetraaza-5,6,11,12-tetraoxaperhydronaphthacene.-

A mixture of 2,3-diacetoxy-1,4-dinitropiperazine (2.92g, 10 mmol), methylenedinitramine (1.36g, 10 mmol), p-dioxane-2,3-diol (1.20g, 10 mmol), and boron trifluoride etherate (3 mL, 3.46g, 22.4 mmol) in trifluoroacetic acid was stirred at room temperature for 18 h. The precipitate was filtered to give 1.17g (53.4%) of white solid: MP darkens at ~270°C and carbonizes above 300°C. The <sup>1</sup>H NMR spectrum showed only traces of the perhydroanthracene. Recrystallization from DMF-ethanol gave 863mg (39.4%) of the perhydronaphthacene: MP - carbonizes above 300°C. The NMR spectrum of this product indicated that it was stereochemically more complex than the product isolated above.

2,3-Dehydro-1,4-dinitropiperazine (24).-

(a) From 2,3-dibromo-1,4-dinitropiperazine and triethyl phosphite. A mixture of the dibromide (2.67g, 8 mmol) and triethylphosphite (10 mL) was stirred at room temperature for 18 h. Hexane (10 mL) was added and the solid was filtered to yield 1.32g (95%) of yellow solid: MP 127°C (dec); <sup>1</sup>H NMR (Me<sub>2</sub>CO-d<sub>6</sub>): δ 4.59 (s, 4H, CH<sub>2</sub>), 7.19 (s, 2H, CH); mass spectrum (CI, CH<sub>4</sub>) m/z 83 (100), 128 (52), 175 (M+1, 2.4). The product reacted with bromine in CH<sub>2</sub>Cl<sub>2</sub> to regenerate the dibromide in 65% yield.

Anal. Calcd for C<sub>4</sub>H<sub>6</sub>N<sub>4</sub>O<sub>4</sub>: C, 27.59; H, 3.47; N, 32.18. Found: C, 27.59; H, 3.49; N, 31.93.

(b) From the dibromide and methylsulfinylcarbanion.- A stirred mixture of DMSO (15 mL) and THF (5 mL) was cooled to 0°C and *n*-butyllithium (4.58 mL of 2.4M in hexane, 11 mmol) was added. The dibromide (1.67g, 5 mmol) in THF (5 mL) was then added dropwise over 5 min. The dark solution was stirred at room

temperature for 45 min, then poured into a mixture of ice and water (70 mL). Filtering gave 630mg (72.3%) of tan solid: MP 123°C (dec). The solid was dissolved in  $\text{CH}_2\text{Cl}_2$  and filtered through a short column of silica gel. Evaporation of the solvent gave yellow crystals: MP 127°C (dec).

(c) From the dibromide and potassium cyanide.- A stirred solution of the dibromide (1.0g, 3 mmol) in DMF was cooled to 0°C and potassium cyanide (651mg, 10 mmol) was added. The solution was warmed to room temperature over 30 min and the DMF was then evaporated under reduced pressure at 50°C. The red residue was diluted with water (15 mL), cooled in ice and then filtered to give 450mg (86.2%) of yellow solid: MP 126°C (dec).

(d) From the dibromide and lithium azide.- A stirred solution of the dibromide (2.0g, 6 mmol) in DMF (10 mL) was cooled to 0°C and a solution of lithium azide (979mg, 20 mmol) in DMF (15 mL) was added over 15 min. The reaction mixture becomes orange and nitrogen is evolved. After warming to room temperature over 1 h, the DMF was evaporated under reduced pressure at 50°C and the residue was diluted with water (30 mL). Cooling this in ice and then filtering gave 823mg of pale yellow solid: MP 105-106°C (dec). The  $^1\text{H}$  NMR spectrum ( $\text{Me}_2\text{CO}-d_6$ ) showed that this product contained about 16% of 2,3-diazido-1,4-dinitropiperazine in addition to the unsaturated dinitramine.

2,3,5,6-Tetraacetoxy-1,4-dinitropiperazine and 2,5-diacetoxy-3,6-dinitrato-1,4-dinitropiperazine.- Anhydrous nitric acid (40 mL) was added dropwise to a stirred suspension of disodium 2,3,5,6-tetrahydroxy-1,4-disulfuric acid (20g, 54.6 mmol) in acetic anhydride (60 mL) over 15 min, while the temperature was maintained at ~30°C. The temperature was kept at 30°C for an additional 30 min by occasional cooling with a cold water bath. Stirring was continued for 2 h longer as the temperature slowly dropped to room temperature. The mixture was then poured into a mixture of ice and water (300 mL) and the resulting white paste was washed several times with cold water by decantation. The paste was squeezed with a flat spatula to remove most of the water and then dissolved in a mixture of acetic anhydride and acetic acid (v:v, 1:1, 200 mL). Sulfuric acid (2 drops) was then added and the solution was heated slowly in an oil bath. A vigorous evolution of nitrogen oxides occurs between 40-70°C (decomposition of some acetyl nitrate), and the temperature was then raised to reflux for 4 h. The nearly colorless solution was evaporated under vacuum at 50°C and the residue triturated with ether (40 mL) and filtered to give 9.25g (39.6%) of the crude tetraacetate as a white solid: MP 255-260°C. Recrystallization from ethanol gave the pure material: MP 266-268°C.

The ether filtrate was cooled in a refrigerator for several days to deposit 2.30g (9.9%) of the diacetoxy dinitrato product: MP 157-161°C. Recrystallization from  $\text{CH}_3\text{CN}$ -isopropyl ether gave white crystals: MP 169-170°C.

2,3,4,6-Tetrabromo-1,4-dinitropiperazine (25).- A solution of 2,3,4,6-tetraacetoxy-1,4-dinitropiperazine (4.08g, 10 mmol) in  $\text{CH}_2\text{Cl}_2$  (100 mL) was cooled to 0°C and boron tribromide (40 mL of 1.0M in  $\text{CH}_2\text{Cl}_2$ ) was added. The solution was stirred at 0°C for 5 min and then warmed to room temperature during 1 h. The mixture was diluted with  $\text{CH}_2\text{Cl}_2$  (100 mL) and washed with water, 5% aqueous  $\text{NaHCO}_3$ , saturated salt solution, dried ( $\text{MgSO}_4$ ) and evaporated to leave a white solid. Trituration with isopropyl ether and filtering gave 4.50g (91.5%) of product: MP 147-148°C (dec). Recrystallization from benzene gave colorless prisms: MP 154-155°C (dec);  $^1\text{H}$

NMR ( $\text{CD}_2\text{Cl}_2$ ):  $\delta$  7.34 (s, 4H, CH); mass spectrum (CI,  $\text{CH}_4$ )  $m/z$  81 (100), 409 (4), 411 (9.8), 413 (9.3), 415 ( $M+1-\text{HBr}$ , Br = 81, 3.7), 525 ( $M+29$ , Br = 81, 0.14).

Anal. Calcd for  $\text{C}_4\text{H}_4\text{Br}_4\text{N}_4\text{O}_4$ : C, 9.77; H, 0.82; N, 11.39; Br, 65.00. Found: C, 9.80; H, 0.78; N, 11.28; Br, 64.75.

Similarly, 2,5-diacetoxy-3,6-dinitrato-1,4-dinitropiperazine was brominated with  $\text{BBr}_3$  to the tetrabromopiperazine in 95% yield.

Bis-tetrazolodehydropiperazine (30).- A stirred solution of lithium azide (2.94g, 60 mmol) in DMF (35 mL) was cooled to  $0^\circ\text{C}$  during the dropwise addition of 2,3,5,6-tetrabromo-1,4-dinitropiperazine (2.95g, 6 mmol) in DMF (25 mL) over 15 min. The mixture was stirred at  $0^\circ\text{C}$  for 5 min longer and then warmed to room temperature during 1 h. The DMF was evaporated under reduced pressure at  $50^\circ\text{C}$  and the residue was diluted with ice-cold water (25 mL). The mixture was cooled in an ice bath for 10 min longer and then filtered to give 450mg (46.2%) of yellow solid: MP  $259^\circ\text{C}$  (violent dec). Recrystallization from methyl isobutyl ketone gave yellow prisms: MP  $264^\circ\text{C}$  (violent dec) - darkening above  $200^\circ\text{C}$ .  $^1\text{H}$  NMR ( $\text{Me}_2\text{CO}-d_6$ ):  $\delta$  9.32 (s, 2H); mass spectrum (CI,  $\text{CH}_4$ )  $m/z$  43 (100), 163 ( $M+1$ , 44).

Anal. Calcd for  $\text{C}_4\text{H}_2\text{N}_8$ : C, 29.63; H, 1.24; N, 69.12. Found: C, 29.60; H, 1.14; N, 69.46.

2,3-Dibromo-5,6-dehydro-1,4-dinitropiperazine (27).-

(a) From 2,3,5,6-tetrabromo-1,4-dinitropiperazine and potassium cyanide. A stirred solution of the tetrabromide (984mg, 2 mmol) in DMF (25 mL) was cooled to  $0^\circ\text{C}$  and potassium cyanide (1.30g, 20 mmol) was added all at once. Stirring was continued at  $0^\circ\text{C}$  for 5 min, and the mixture was then warmed to room temperature over 30 min. The DMF was evaporated under vacuum at  $50^\circ\text{C}$ , and the dark red residue was diluted with ice-cold water (20 mL) and cooled in an ice bath for 15 min. The precipitate was filtered, washed with water, and dried to give 335mg (50.4%) of almost white solid: MP  $82^\circ\text{C}$  (dec);  $^1\text{H}$  NMR ( $\text{Me}_2\text{CO}-d_6$ ):  $\delta$  7.47 (s, 2H, CH), 7.73 (s, 2H, CHBr); mass spectrum (CI,  $\text{CH}_4$ )  $m/z$  81 (100), 284 (.4), 286 (17.7), 288 ( $M+1-\text{HNO}_2$ , Br = 81, 8.8), 331 (0.4), 333 (0.74), 335 ( $M+1$ , Br = 81, 0.3).

The dibromoolefin slowly decomposed upon standing at room temperature for several days. It could be stored in a refrigerator at  $0^\circ\text{C}$  for over a month without appreciable decomposition. In solution (acetone,  $\text{CH}_2\text{Cl}_2$ ) it decomposed completely within 2 h.

(b) From the tetrabromide and potassium fluoride.- To a stirred solution of the tetrabromide (492mg, 1.0 mmol) in DMSO (3 mL) was added potassium fluoride (581mg, 10 mmol) all at once. After 45 min the mixture was diluted with cold water (15 mL), cooled in ice for 15 min, and then filtered to give 114mg (34.3%) of white solid: MP  $83^\circ\text{C}$  (dec).

2,3-Diazido-5,6-dehydro-1,4-dinitropiperazine (28).- A stirred solution of 2,3-dibromo-5,6-dehydro-1,4-dinitropiperazine (996mg, 3 mmol) in DMF (25 mL) was cooled to  $0^\circ\text{C}$  and lithium azide (1.47g, 30 mmol) was added all at once. The mixture was warmed to room temperature during 1 h and the DMF was then evaporated under vacuum at  $35^\circ\text{C}$ . The residue was diluted with cold water (30 mL), cooled in ice for 10 min, and filtered to give 210mg of white solid. NMR analysis showed that this was a mixture of the diazide and the bis-tetrazolodehydropiperazine in about equal amounts. The solid was dissolved in  $\text{CH}_2\text{Cl}_2$  and filtered through a small column of silica gel. Evaporation of the



solvent gave the pure diazide: MP 95°C (violent dec); IR (KBr) 2160 (sh) and 2120  $\text{cm}^{-1}$  ( $\text{N}_3$ ), 1550, 1265  $\text{cm}^{-1}$  ( $\text{NO}_2$ );  $^1\text{H}$  NMR ( $\text{Me}_2\text{CO}-d_6$ )  $\delta$  7.17 (s, 2H), 7.27 (s, 2H); mass spectrum (CI,  $\text{CH}_4$ )  $m/z$  44 (100), 94 (29), 165 (25), 185 (14), 210 (22), 214 ( $M+1-\text{HN}_3$ , 32), 257 ( $M+1$ , 0.64).

Anal. Calcd for  $\text{C}_4\text{H}_4\text{N}_{10}\text{O}_4$ : C, 18.75; H, 1.57; N, 54.69. Found: C, 18.40; H, 1.58; N, 55.01.

2,3,5,6-Tetranitrato-1,4-dinitropiperazine (31).- Anhydrous nitric acid (7 mL) was stirred and cooled to 0°C during the addition of trifluoroacetic anhydride (10 mL) over 5 min. After 10 min, disodium-2,3-5,6-tetrahydroxy-1,4-disulfuric acid (2.48g, 7 mmol) was added in portions over 5 min. The mixture was stirred at 0°C for 1 h and then at room temperature for 18 h. Volatiles were then removed under reduced pressure and the residue was diluted with ice-cold water (30 mL) and the mixture extracted with  $\text{CH}_2\text{Cl}_2$ . The extracts were washed with 5% aqueous  $\text{NaHCO}_3$ , saturated salt solution, dried ( $\text{MgSO}_4$ ), and evaporated to leave a solid. Trituration of this with isopropyl ether and filtering gave 535mg (18.2%) of white solid: MP 144-145°C (dec). Recrystallization from benzene gave colorless prisms of the same MP:  $^1\text{H}$  NMR ( $\text{Me}_2\text{CO}-d_6$ ):  $\delta$  8.33 (s, 4H, CH); mass spectrum (CI,  $\text{CH}_4$ )  $m/z$  46 (100), 47 (32), 48 (65), 358 ( $M+1-\text{HNO}_3$ , 0.6).

Upon standing in a closed container for 24 h, the colorless prisms became cloudy and opaque. After several days, red fumes of  $\text{NO}_2$  were observed in the container. A satisfactory elemental analysis could not be obtained.

## REFERENCES

1. H. G. Adolph, M. Chaykovsky, J. M. Goldwasser, and W. M. Koppes, "Synthesis of Energetic Materials", Annual Progress Report for the Office of Naval Research, Mar 1984; Naval Surface Weapons Center, Silver Spring, Maryland 20903-5000.
2. We wish to acknowledge the help of Dr. A. P. Manzara, Commercial Chemicals Division/3M in obtaining these and other diol samples.
3. F. D. Trischler and J. Hollander, J. Polym. Science A-1 5, 2343 (1967).
4. P. Johncock, B. P. 1294657 (1972).
5. H. G. Adolph, W. M. Koppes, D. A. Cichra, and M. E. Sitzmann, NSWC MP-82-214 "Synthesis of Energetic Materials", Mar 1982.
6. J. C. Hoffsommer, D. A. Kubose, and D. J. Glover, J. Phys. Chem. 81, 380.
7. A. H. Dinwoodie, J. A. Gibson, and J. B. Parker, J. Chem. Soc. (C) 1967, 496.
8. H. Feuer, G. B. Bachman, and W. May, J. Am. Chem. Soc. 76, 5124 (1954).

# DISTRIBUTION LIST

Prof. J.H. Boyer  
University of Illinois  
Department of Chemistry  
Box 4348  
Chicago Illinois 60680

Prof. J. C. Chien  
University of Massachusetts  
Department of Chemistry  
Amherst, MA 03003

Dr. B. David Halpern  
Polysciences, Inc.  
Paul Valley Industrial Park  
Warrington, PA 18976

Dr. M.B. Frankel  
Rockwell International  
Rocketdyne Division  
6633 Canoga Avenue  
Canoga Park, CA 91304

Dr. R.A. Earl  
Hercules, Inc.  
Magna, Utah 84109

Dr. C. Bedford  
SRI International  
333 Ravenswood Avenue  
Menlo Park, CA 94025

Dr. Robert R. Ryan  
INC-4, MS C346  
Los Alamos National Laboratory  
Los Alamos, New Mexico 87545

Dr. Robert D. Champman  
AFRPL/LKLR  
Edwards AFB, CA 93525

Dr. L. Erwin  
MIT  
Room 35-008  
Cambridge, MA 02139

Dr. M. Farber  
Space Sciences, Inc.  
135 W. Maple Avenue  
Monrovia, CA 91016

Dr. W.H. Graham  
Morton Thiokol, Inc.  
Hunstville Division  
Hunstville, AL 35807-7501

Dr. C. Coon  
Lawrence Livermore Lab.  
University of California  
P.O. Box 808  
Livermore, CA 94550

Dr. R. Gilardi  
Naval Research Laboratory  
Code 6030  
Washington, D.C. 20375

Dr. Alan Marchand  
Dept. of Chemistry  
North Texas State University  
KTSU Station, Box 5068

T.B. Brill  
Department of Chemistry  
University of Delaware  
Newark, Delaware 19716

Dr. Richard A. Hollins  
Naval Weapons Center  
Code 3853  
China Lake, CA 93555

Dr. R. Armstrong  
MIT  
Room 66-505  
Cambridge, MA 02139

Professor Philip E. Eaton  
Department of Chemistry  
University of Chicago  
5735 South Ellis Avenue  
Chicago, IL 60637

Dr. G. Neece  
Office of Naval Research  
Code 413  
Arlington, VA 22217

DISTRIBUTION LIST

Mr. C.M. Havlik  
O/83-10, B/157-3W  
Lockheed Missiles & Space Co., Inc.  
P.O. Box 504  
Sunnyvale, CA 94086

Dr. Philip Howe  
Ballistic Research Laboratory  
Code DRXBR-TBD  
Aberdeen Proving Ground, MD 21005

Prof. C. Sue Kim  
Department of Chemistry  
California State University, Sacramento  
Sacramento, California 95819

Mr. J. Moniz  
Naval Ordnance Station  
Code 5253L  
Indian Head, MD 20640

Dr. R. Reed Jr.  
Naval Weapons Center  
Code 38904  
China Lake, CA 93555

Dr. Kurt Baum  
Fluorochem, Inc.  
680 South Ayon Ave.  
Azusa, CA 91702

Dr. James T. Bryant  
Naval Weapons Center  
Code 32058  
China Lake, CA 93555

Dr. L. Rothstein  
Assistant Director  
Naval Explosives Dev. Engineering Dept.  
Naval Weapons Station  
Yorktown, VA 23691

Dr. Henry Webster, III  
Manager, Chemical Sciences Branch  
ATTN: Code 5063  
Crane, IN 47522

Dr. R.S. Valentini  
United Technologies Chemical Systems  
P.O. Box 50015  
San Jose, CA 95150-0015

Dr. Andrew C. Victor  
Naval Weapons Center  
Code 3208  
China Lake, CA 93555

Dr. V.J. Keenan  
Anal-Syn Lab. Inc.  
P.O. Box 547  
Paoli, PA 19301

P. Politzer  
Chemistry Department  
University of New Orleans  
New Orleans, Louisiana 70148

Mr. David Siegel  
Office of Naval Research  
Code 253  
Arlington, VA 22217

Dr. R. Atkins  
Naval Weapons Center  
Code 3852  
China Lake, CA 93555

L.H. Sperling  
Materials Research Center #32  
Lehigh University  
Bethlehem, PA 18015

Dr. John S. Wilkes, Jr.  
FJSRL/NC  
USAF Academy, CO 80840

Dr. H. Rosenwasser  
Naval Air Systems Command  
AIR-320R  
Washington, D.C. 20361

Dr. A. Nielsen  
Naval Weapons Center  
Code 385  
China Lake, CA 93555

Dr. Joyce J. Kaufman  
The Johns Hopkins University  
Department of Chemistry  
Baltimore, MD 21218

DISTRIBUTION LIST

Defense Technical Information Center  
Bldg. 5, Cameron Station  
Alexandria, VA 22314  
(12 copies)

Arpad Juhasz  
Code DRDAR-IBD  
Ballistic Research Lab  
Aberdeen, MD 21005

Dr. Robert J. Schmitt  
SRI International  
333 Ravenswood Avenue  
Menlo Park, CA 94025

Mr. J. Consaga  
Naval Surface Weapons Center  
Code R-16  
Indian Head, MD 20640

Naval Sea Systems Command  
ATTN: Mr. Charles M. Christensen  
NAVSEA62R2  
Crystal Plaza, Bldg. 6, Rm 806  
Washington, D.C. 20362

Mr. R. Beauregard  
Naval Sea Systems Command  
SEA 64E  
Washington, D.C. 20362

Dr. Anthony J. Matuszko  
Air Force Office of Scientific Research  
Directorate of Chemical & Atmospheric  
Sciences  
Bolling Air Force Base  
Washington, D.C. 20332

J.J. Rocchio  
USA Ballistic Research Lab.  
Aberdeen Proving Ground, MD 21005-5066

G.A. Zimmerman  
Aerojet Tactical Systems  
P.O. Box 13400  
Sacramento, CA 95813

B. Swanson  
Inc-4 MS C-346  
Los Alamos National Laboratory  
Los Alamos, New Mexico 87545

Dr. J.R. West  
Morton Thiokol, Inc.  
P.O. Box 30058  
Shreveport, LA 71130

Director  
Naval Research Laboratory  
Attn: Code 2627  
Washington, D.C. 20375  
(6 copies)

Dr. Michael D. Coburn  
Los Alamos National Lab  
M-1, Explosives Technology  
Mail Stop, C920  
Los Alamos, NM 87545

Dr. L.H. Caveny  
Air Force Office of Scientific  
Research  
Directorate of Aerospace  
Sciences  
Bolling Air Force Base  
Washington, D.C. 20332

W.G. Roger  
Code 5253  
Naval Ordnance Station  
Indian Head, MD 20640

Dr. Donald L. Bell  
Air Force Office of Scientific  
Research  
Directorate of Chemical &  
Atmospheric Sciences  
Bolling Air Force Base  
Washington, D.C. 20332

U.S. Army Research Office  
Chemical & Biological Sciences  
Division  
P.O. Box 12211  
Research Triangle Park, NC  
27709

G. Butcher  
Hercules, Inc.  
MS X2H  
P.O. Box 98  
Magna, Utah 84044

# DISTRIBUTION LIST

W. Waesche  
Atlantic Research Corp.  
7511 Wellington Road  
Gainesville, VA 22065

Dr. Janet Wall  
Code 012  
Director, Research Administration  
Naval Postgraduate School  
Monterey, CA 93943

R.E. Shenton  
Atlantic Research Corp.  
7511 Wellington Road  
Gainesville, VA 22065

Mike Barnes  
Atlantic Research Corp.  
7511 Wellington Road  
Gainesville, VA 22065

Dr. Lionel Dickinson  
Naval Explosive Ordnance  
Disposal Tech. Center  
Code D  
Indian Head, MD 20340

M.H. Miles  
Dept. of Physics  
Washington State University  
Pullman, WA 99164-2814

Dr. T.F. Davidson  
Vice President, Technical  
Aerospace Group  
110 North Wacker Drive  
Chicago, IL 60606

Dr. D. Mann  
U.S. Army Research Office  
Engineering Division  
Box 12211  
Research Triangle Park, NC 27709-2211

Mr. L. Roslund  
Naval Surface Weapons Center  
Code R10C  
White Oak, Silver Spring, MD 20903-5000

Mr. R. Geisler  
ATTN: DY/MS-24  
AFRPL  
Edwards AFB, CA 93523

Dr. D.D. Dillehay  
Morton Thiokol, Inc.  
Longhorn Division  
Marshall, TX 75670

G.T. Bowman  
Atlantic Research Corp.  
7511 Wellington Road  
Gainesville, VA 22065

Brian Wheatley  
Atlantic Research Corp.  
7511 Wellington Road  
Gainesville, VA 22065

Mr. G. Edwards  
Naval Sea Systems Command  
Code 62R32  
Washington, D.C. 20362

Prof. John Deutch  
MIT  
Department of Chemistry  
Cambridge, MA 02139

Dr. E.H. deButts  
Hercules Aerospace Co.  
P.O. Box 27408  
Salt Lake City, UT 84127

David A. Flanigan  
Director, Advanced Technology  
Morton Thiokol, Inc.  
Aerospace Group  
110 North Wacker Drive  
Chicago, IL 60606

Dr. Randy Peters  
Aerojet Strategic Propulsion  
Co.  
Bldg. 05025 - Dept. 5400 - MS  
167  
P.O. Box 15699C  
Sacramento, CA 95813

Dr. David C. Sayles  
Ballistic Missile Defense  
Advanced Technology Center  
P.O. Box 1500  
Huntsville, AL 35807

DISTRIBUTION LIST

Naval Air Systems Command  
ATTN: Mr. Bertram P. Sobers  
NAVAIR-320G  
Jefferson Plaza 1, RM 472  
Washington, D.C. 20361

R.B. Steele  
Aerojet Strategic Propulsion Co.  
P.O. Box 15699C  
Sacramento, CA 95813

Mr. E.S. Sutton  
Thiokol Corporation  
Elkton Division  
P.O. Box 241  
Elkton, MD 21921

Dr. Grant Thompson  
Morton Thiokol, Inc.  
Wasatch Division  
MS 240 P.O. Box 524  
Brigham City, UT 84302

Dr. R.S. Miller  
Office of Naval Research  
Code 432P  
Arlington, VA 22217  
(10 copies)

JHU Applied Physics Laboratory  
ATTN: CPIA (Mr. T.W. Christian)  
Johns Hopkins Rd.  
Laurel, MD 20707

Dr. Kenneth D. Hartmann  
Hercules Aerospace Division  
Hercules Incorporated  
Alleghany Ballistic Lab.  
P.O. Box 210  
Washington, D.C. 21502

Mr. Otto K. Heiney  
AFATL-DLJG  
Elgin AFB, FL 32542  
MD

Dr. Merrill K. King  
Atlantic Research Corp.  
5390 Cherokee Avenue  
Alexandria, VA 22312

Director  
US Army Ballistic Research Lab  
ATTN: DRXBR-IBD  
Aberdeen Proving Ground, MD  
21005

Commander  
US Army Missile Command  
ATTN: DRSMI-RKL  
Walter W. Wharton  
Redstone Arsenal, AL 35898

Dr. Ronald L. Derr  
Naval Weapons Center  
Code 389  
China Lake, CA 93555

T. Boggs  
Naval Weapons Center  
Code 389  
China Lake, CA 93555

Lee C. Estabrook, P.E.  
Morton Thiokol, Inc.  
P.O. Box 30058  
Shreveport, LA 71130

Dr. A.L. Slafkosky  
Scientific Advisor  
Commandant of the Marine Corps  
Code RD-1  
Washington, D.C. 20380

Dr. Henry P. Marshall  
Dept. 93-50, Bldg. 204  
Lockheed Missile & Space Co.  
3251 Hanover St.  
Palo Alto, CA 94304

Dr. Ingo W. May  
Army Ballistic Research Lab.  
ARRADCOM  
Code DRXBR - 1BD  
Aberdeen Proving Ground,  
21005

P.A. Miller  
736 Leavenworth Street, #6  
San Francisco, CA 94109

**END**

**FILMED**

**7-85**

**DTIC**